



Cite this: *Nanoscale*, 2018, **10**, 13449

A novel combined experimental and multiscale theoretical approach to unravel the structure of SiC/SiO_x core/shell nanowires for their optimal design†

Tommaso Morresi,^{a,b} Melanie Timpel,^b *c,d Andrea Pedrielli,^{a,b} Giovanni Garberoglio,^a Roberta Tatti,^d Roberto Verucchi,^d Luca Pasquali,^{e,f,g} Nicola Maria Pugno,^{b,h,i} Marco Vittorio Nardi,^b *c,d and Simone Taioli,^b *a,j

In this work we propose a realistic model of nanometer-thick SiC/SiO_x core/shell nanowires (NWs) using a combined first-principles and experimental approach. SiC/SiO_x core/shell NWs were first synthesised by a low-cost carbothermal method and their chemical–physical experimental analysis was accomplished by recording X-ray absorption near-edge spectra. In particular, the K-edge absorption lineshapes of C, O, and Si are used to validate our computational model of the SiC/SiO_x core/shell NW architectures, obtained by a multiscale approach, including molecular dynamics, tight-binding and density functional simulations. Moreover, we present *ab initio* calculations of the electronic structure of hydrogenated SiC and SiC/SiO_x core/shell NWs, studying the modification induced by several different substitutional defects and impurities into both the surface and the interfacial region between the SiC core and the SiO_x shell. We find that on the one hand the electron quantum confinement results in a broadening of the band gap, while hydroxyl surface terminations decrease it. This computational investigation shows that our model of SiC/SiO_x core/shell NWs is capable to deliver an accurate interpretation of the recorded X-ray absorption near-edge spectra and proves to be a valuable tool towards the optimal design and application of these nanosystems in actual devices.

Received 7th May 2018,
Accepted 27th June 2018
DOI: 10.1039/c8nr03712d
rsc.li/nanoscale

1 Introduction

In recent decades, the discovery and synthesis of novel silicon (Si) nanostructures, such as Si dots and nanowires (NWs), have contributed to the rapid advancement of nano-science and nano-technology¹ to produce *e.g.* small transistors,² light emit-

ting devices³ or spin qubits for quantum computers.⁴ Moreover, featuring one-dimensional (1D) geometry and high aspect ratio at the nanoscale,⁵ Si nanostructures brought about fundamental interest in the scientific community to study the effect of reduced dimensionality onto excitons and electron–electron interaction.^{6,7} In particular, Si NWs were found capable to achieve outstanding performances in catalysis,⁸ energy harvesting^{9,10} and storage,^{11,12} chemical and biological sensing,^{13,14} as well as application in biomedicine.¹⁵

However, while a wide range of remarkable characteristics, most notably abundancy and the possibility of doping-induced modification of the electrical properties, makes Si by far the most widely used material for making electronics and optoelectronic devices, silicon carbide (SiC) offers wider band gap, larger critical electric fields and breakdown voltage, higher thermal conductivity and maximum operating temperature. These features make it probably the most promising alternative to replace Si in electronics devices working at high power/frequency or under prohibitive conditions.¹⁶ Despite these peculiar properties, the use of SiC in electronics is not widespread. Major reasons for this are the high cost of

^aEuropean Centre for Theoretical Studies in Nuclear Physics and Related Areas (ECT*–FBK) and Trento Institute for Fundamental Physics and Applications (TIFPA–INFN), Trento, Italy. E-mail: morresi@ectstar.eu, taioli@ectstar.eu

^bLaboratory of Bio-Inspired and Graphene Nanomechanics, Department of Civil, Environmental and Mechanical Engineering, University of Trento, Italy

^cDepartment of Industrial Engineering, University of Trento, Italy. E-mail: melanie.timpel@unit.it, marcovittorio.nardi@unitn.it

^dIMEM – CNR, Institute of Materials for Electronics and Magnetism, Trento unit, Trento, Italy

^eIOM–CNR Institute, Trieste, Italy

^fEngineering Department, University of Modena e Reggio Emilia, Italy

^gDepartment of Physics, University of Johannesburg, South Africa

^hKet-Lab, Edoardo Amaldi Foundation, Italian Space Agency, Rome, Italy

ⁱSchool of Engineering and Materials Science, Queen Mary University of London, UK

^jFaculty of Mathematics and Physics, Charles University, Prague, Czech Republic

†Electronic supplementary information (ESI) available: Further details on *ab initio* simulations and experiments. See DOI: 10.1039/C8NR03712D

production^{17–19} and the high density of defects at the interface with the oxides in microelectronics applications.^{20,21}

In particular, the synthesis of 1D SiC structures has attracted great interest due to the possibility of combining the material's unique physical/chemical characteristics with low dimensionality.^{22–24} The carbide mechanical properties are enhanced in NWs, showing super-plasticity at low temperature²⁵ and higher strength so that they can be used for toughening composite materials.²⁶ Furthermore, SiC nanowires show efficient electromagnetic wave absorption,^{27,28} and their electronic properties have been exploited to realize field effect transistors²⁹ and efficient field emission sources.³⁰

One common feature of Si-based NWs, regardless of the growth technique, is the presence of an amorphous silicon oxide (SiO_x) external layer coating the nanostructure.²⁴ By tuning the oxide layer thickness with respect to the SiC NW diameter in a core/shell architecture^{31–33} one can modify both the electron emission^{34,35} and the optical^{32,36,37} properties of these systems. In addition, the SiO_x layer offers facile strategies to anchor organic molecules on the NWs' surface by chemical methods, paving the way for applications of functionalized SiC/SiO_x core/shell NWs in several fields, such as protective coatings,³⁸ biosensing³⁹ or as hybrid nanosystems for biomedical applications.⁴⁰

In this regard, it has been shown that SiC/SiO_x core/shell NWs coated with light-absorbing organic molecules (so-called photosensitizers) can be efficiently applied in anti-cancer therapy using X-ray excitation,⁴⁰ since the energy absorbed by the X-ray excited inorganic NWs can be efficiently transferred to the photosensitizer that generates highly reactive oxygen species, which in turn have cytotoxic effects.⁴¹

To exploit the intriguing and remarkable features offered by SiC/SiO_x core/shell architectures, one must characterize accurately their chemical–physical properties, in particular by investigating both the SiO_x outer shell and the SiC/SiO_x buried interface, typically populated by defects, *e.g.* carbonaceous contaminants, oxycarbides related to the carbide oxidation process,⁴² and oxide impurities that can dramatically modify and deteriorate the electrical properties of electronic and optoelectronic devices.^{43,44} In this respect, a variety of experimental techniques have been routinely used to determine structural and also chemical properties of the SiC/SiO₂ interface, such as transmission electron microscopy (TEM),⁴⁵ photoemission electron spectroscopy (PES)^{46–48} and X-ray absorption near-edge spectroscopy (XANES).^{49,50} The latter, in particular, revealed to be a powerful tool for investigating nanostructured materials and inner interfaces.^{6,51} However, state-of-the-art computational investigations are limited to the crystalline phases of SiC nanowires,^{52–56} while the SiC/SiO_x interface is modeled only in the case of regular geometries such as slabs or nanodots.^{57,58} Furthermore, these models are not enough accurate and realistic for shedding light on the many electronic and structural information enclosed in XANES spectra, and to explain the absorption peak lineshape of several transitions arising from these structures. In order to obtain a reliable picture for linking structural features to absorption

peaks, a fully atomistic model of SiC/SiO_x core/shell NWs, including adventitious carbon, defects and contaminants has still to be developed.

In this work, we thus analyse first the structural arrangements and composition of SiC/SiO_x core/shell NWs using multiscale modeling; second, we investigate the electronic and optical properties of these nanostructures characterized by various defects and impurities by comparing *ab initio* simulations of absorption spectra (XANES) with recorded experimental data on in-house grown NWs to characterize these systems and eventually validate our computational model. This analysis led us to devise a realistic model of SiC/SiO_x core/shell NWs that includes the interface region between the two different materials, that is the amorphous SiO_x shell and the SiC core nanowire. The synergic use of computational and experimental tools delivers a comprehensive and more accurate chemical–physical description of SiC/SiO_x core/shell NWs, paving the way towards their use in power electronics, nanomedicine, and many other applications requiring high endurance.

2 Experimental details

The SiC/SiO_x core/shell NWs were grown *via* a bottom-up carbothermal method, based on the reaction between carbon monoxide and the native oxide on (001) Si substrates, using iron oxide as a catalyst.^{31,36} The core/shell structure of a single NW with diameter of ~60 nm is represented in Fig. 1(a), reporting the TEM axial and cross-sectional views. As a reference for the SiC/SiO_x interface (SiC core NWs without shell), the SiO_x was fully removed from the as-grown NWs by etching the substrates in hydrofluoric acid (HF) (1 : 3) aqueous solution for an extended period of 60 min. NWs without SiC core (denoted as SiO_x NWs) were grown by omitting the carbon monoxide precursor and are used as a reference for SiO₂.

Synchrotron measurements were performed at the BEAR beamline (BL8.1L) of the ELETTRA synchrotron facility (Italy) and at the Spherical Grating Monochromator (SGM) beamline of the Canadian Light Source, University of Saskatchewan (Canada). The BEAR beamline provides a photon energy range of 3–1600 eV with a resolution of $E/\Delta E \sim 3000$ and an incident photon flux (i.f.) of $\sim 1 \times 10^9$ photons per s for C K-edge studies, whereas the SGM beamline provides a photon energy range of 250–2000 eV with the resolution of $E/\Delta E \sim 5000$ for Si K-edge (i.f. $\sim 1 \times 10^{11}$ photons per s) and O K-edge (i.f. $\sim 1 \times 10^{12}$ photons per s) measurements. XANES spectra were collected from all three types of NWs, *i.e.*, as-grown SiC/SiO_x core/shell, SiO_x and HF-etched SiC NW ensembles that were maintained on the planar substrates.

The spectra were collected in total electron yield (TEY) mode (*i.e.*, drain current mode) in the energy range 270–320 eV, 510–570 eV and 1830–1880 eV corresponding to the C, O and Si K-edge, respectively. XANES data were normalized to the corresponding spectrum acquired on a photodiode at the end of the beamline. The energy scale of each single spectrum was

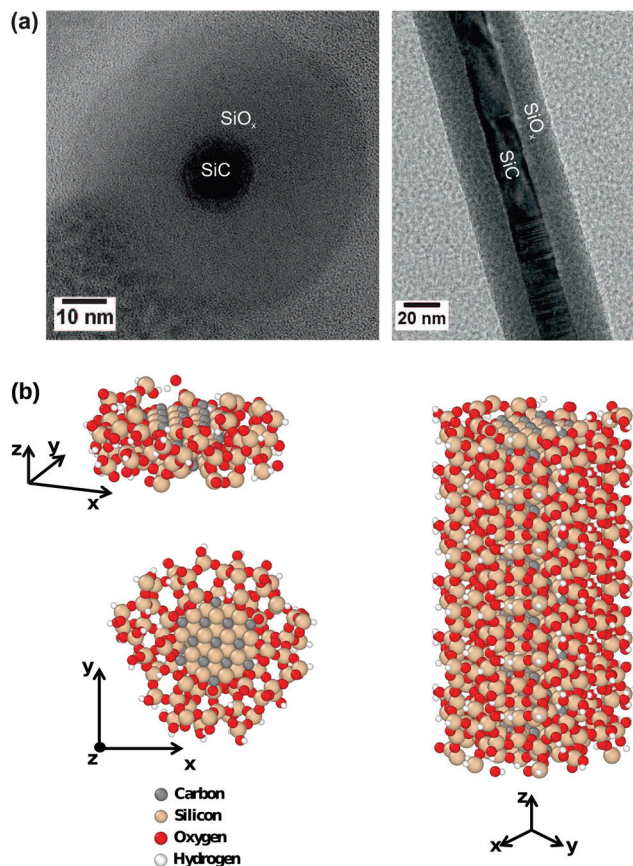


Fig. 1 (a) TEM images adapted from ref. 36 and 63 of a SiC/SiO_x core/shell NW in axial view (left panel) and cross-sectional view (right panel). (b) Computational model of a single SiC/SiO_x core/shell NW; left panel shows the NW unit cell side view (upper part) and top view (lower panel); right panel shows a side view of the NW supercell obtained by periodically repeating the unit cell along the rotational symmetry axis direction.

re-calibrated taking into account the energy fluctuations of characteristic absorption features measured on the refocusing mirror and Au mesh, respectively.

3 Computational details

3.1 Modeling of SiC and SiC/SiO_x core/shell NWs

The steps performed to obtain a fully realistic model of SiC/SiO_x core/shell NWs, similar to the typical structure shown in Fig. 1(a), are the following: generation of the pristine SiC NW core, passivation of the SiC NW surface with different chemical elements, and creation of the SiO_x outer shell by embedding the SiC core. These three steps are described one by one in the following sections.

3.1.1 Structure of the SiC core. The SiC nanowires (NWs) were obtained by cleaving a cylinder out of a 3C-SiC supercell along the [111] direction, which represents the growth axis in our synthesis process. In particular, using a cubic cell with lattice parameter $a = 4.348 \text{ \AA}$ for the 3C-SiC crystal structure,

one obtains a simulation supercell for the NW with an axial periodicity of $a\sqrt{3} = 7.5309 \text{ \AA}$. The z direction identifies the cylindrical symmetry axis of the NW (the cylindrical symmetry is removed by coating with SiO_x). The size of the calculation supercell was chosen equal to 50 \AA in the transverse direction, that is large enough to avoid spurious interactions between periodic images, even in the case of the NWs with the largest diameter (26 \AA). Pristine SiC NWs are forcefully characterized by the presence of contaminants at the surface. The latter dramatically modify the electronic and optical properties of these nanosystems.^{59,60} In the following section we thus thoroughly assess these effects.

3.1.2 Surface passivation of the SiC core. Surface-related states have a large impact in systems at nanoscale and appear usually as intra-gap states.⁵⁴ In particular, the terminations of the dangling bonds present on the SiC NW surface can affect dramatically the electronic structure and, thus, must be carefully investigated.

To perform the analysis of possible surface contaminants, we have saturated the dangling bonds of C and Si superficial atomic centers by using different atomic species and chemical compounds, notably -H atoms and hydroxyl groups (-OH). Indeed, oxidized OH-SiC NWs can help our understanding of the SiC core/SiO_x shell interface in the HF-etched SiC NW samples, which consists of a thin layer of silicon oxycarbides.³⁶

The optimized configurations of these saturated NWs were obtained by using the Self-Consistent Charge Density Functional Tight Binding (SCC-DFTB) approach, implemented in the DFTB+ code suite.⁶¹ To perform the DFTB structural and electronic relaxations we used the Slater-Koster parameter set matsci-0-3⁶² and we included the d-orbitals in the local basis set of the silicon atoms, which are essential to achieve accurate band gap and band structure (for further detail see ESI, subsection 1.1†). Electronic structure simulations were carried out in the unit cell using a $1 \times 1 \times 4$ k -point grid sampling. Forces among all atoms within the supercell are relaxed below 0.05 eV \AA^{-1} .

In agreement with previous *ab initio* studies,⁵⁴ we find that the -OH termination is stable at the surface of the NW. This configuration is more stable than that one with unsaturated O atoms; moreover, -OH impurities are preferentially anchored to the Si atom at the surface, presenting formation energies of 1.76 and 3.82 eV for the C-OH and Si-OH configuration, respectively.⁵⁴

In the case of -H passivation the band gap decreases by increasing the size of the radius, and tends asymptotically to the bulk value, which from our calculations is 2.3 eV (experimentally the band-gap of crystalline 3C-SiC is 2.36 eV.⁶⁴ We notice that the band gap for a 1.2 nm diameter NW is 3.3 eV (see Table 1). This value is rather different from the one obtained by using the full density functional (DFT) approach, which is 2.7 eV, in agreement with previous DFT simulations.^{54,55} Nevertheless, this difference is consistent with the value of the 3C-SiC Γ point energy gap (which is larger than the fundamental band gap) found to be 1.41 eV from full DFT

Table 1 Band gap of the SiC core NW terminated with –H atoms or –OH radicals as computed by DFTB

Radius (nm)	Band gap (eV)	
	–H sat.	–OH sat.
0.6	3.30	2.55
0.9	2.79	2.10
1.3	2.52	2.05

calculations. DFTB band-gap (2.3 eV), possibly because of the Slater–Koster parametrization, is very much close to the measured band gap (2.36 eV) with respect to that obtained by DFT. These findings make us confident that DFTB can be safely used to describe the chemical-physics of the SiC NWs. By passivating the superficial dangling bonds of the SiC NW with –OH we find a similar behaviour of the band gap, monotonically and asymptotically decreasing with the increasing diameter (see Table 1).

The major finding of our electronic band structure simulations (see Fig. S7 and S9 of ESI† for the NWs' band structure) is that both H-SiC and OH-SiC NWs turn into a direct band-gap semiconductor, with the minimum distance between the valence band maximum (VBM) and the conduction band minimum (CBM) at the Γ point. This change is basically due to electron quantum confinement obtained by reducing the system dimensionality from 3D to 1D. Nevertheless, the band-gap calculated for the two terminations is rather different at the same radius (see Table 1), that is consistently lower in the case of –OH termination.

This difference can be rationalized in terms of both chemical termination and quantum confinement. Indeed, these two effects compete with each other and affect the electronic behaviour of the nanosystem. Quantum confinement tends to increase the band gap and largely influences systems mostly at the nanoscale, as asymptotically the band gap must match the bulk value of 3C-SiC almost independently of the surface termination. At small radius, we find that the Mulliken charge distribution of the atoms close to the surface is rather homogeneous in the case of –H termination, while using –OH passivation the superficial atoms are partially deprived of their charge due to the high electronegativity of oxygen atoms (see ESI (sub section 1.1†)). Thus, surface states are more likely to appear and to affect more significantly the –OH terminated SiC NW, reducing the band gap with respect to the –H passivated NW. Furthermore, we find that the band gap of the oxidized OH-SiC NWs is free from defective states and that the OH-SiC NWs are non-magnetic systems (see Fig. S6 of ESI†).

To reinforce our conclusions on the effects induced by different passivations of the NW surface, drawn on the basis of the Mulliken charge population analysis, we notice that also the calculation of the HOMO and LUMO probability densities (square modulus of the wavefunctions) of the H-SiC and OH-SiC NWs may shed some light on the chemical–physical modifications leading to the measured XANES spectral line shape. Thus, in Fig. S10 and S11 of the ESI† we plot the VBM

and CBM real-space probability densities for the smallest radius NW. In particular, we notice that in the case of –H terminated NWs both the VBM (left hand side of Fig. S10†) and the CBM (left hand side of Fig. S10†) are localized in the core of the NW, while in the case of –OH termination the VBM (left hand side of Fig. S11†) is localized on the oxygen atoms and the CBM (right hand side of Fig. S11†) remains mostly core-localized. This different spatial distribution of the CBM and VBM can be attributed to the strong electronegativity of the oxygen atomic species.

In the following simulations we decided to use the 0.6 nm radius SiC NW, due to the high computational cost for treating larger wires. Furthermore, due to the fact that XANES is a probe of the local environment, we expect that this model system is sufficient to reproduce accurately XANES experimental data.

3.1.3 SiC/SiO_x core/shell nanowire. The amorphous SiO_x outer shell was built above the 0.6 nm radius SiC core by using molecular dynamics (MD) with reactive potentials (ReaxFF⁶⁵). In particular, the parametrization of the forces has been chosen⁶⁶ to reproduce SiO_x and SiC structures at different stoichiometry. To perform these simulations we used the LAMMPS code.⁶⁷ The interface between SiC and SiO_x was created by saturating the C and Si dangling bonds protruding from the surface of the SiC NW core with oxygen atoms, and by adding Si–O groups in order to have Si tetrahedrally coordinated with oxygen atoms (see Fig. S12 of ESI, sub section 1.2†, for further details). In this way the number of bonds at the interface is decreased by a factor 2.3 to better match the density of stoichiometric SiO₂. Finally, a MD run was performed to optimize and rearrange the outer shell atomic configurations, while the remaining dangling bonds were saturated by means of hydrogen atoms. The final structure of the model SiC/SiO_x core/shell NW, reported in Fig. 1(b), has been further characterized with respect to bond lengths and relative angle distributions, finding a good agreement with the literature (for more details about structural modeling and characterization see ESI, sub section 1.2†, and sub section 1.3†, respectively).

3.2 Electronic structure simulations of the SiC/SiO_x core/shell nanowire

The SiC/SiO_x core/shell NW model has been characterized by computing the electronic band structure and the DOS using SCC-DFTB. In Fig. 2(a) we report both the total DOS and the local DOS (LDOS) obtained by projecting onto the atoms belonging to different radial shells, which are represented in dark brown in Fig. 2(b).

We notice that the LDOSs reproduce unambiguously the different NW building blocks. Indeed, for $R \leq 0.4$ nm, which means within the NW core, both the LDOS (red and green curves in Fig. 2(a)) and the band gap correspond to those of a SiC NW; for $R \geq 0.84$ nm the LDOS and the band gap are related to those of amorphous SiO_x (blue curve in 2(a)); finally for R in the range 0.4–0.84 nm, corresponding to the interface region, we find a shape of the LDOS (brown curve in Fig. 2(a))

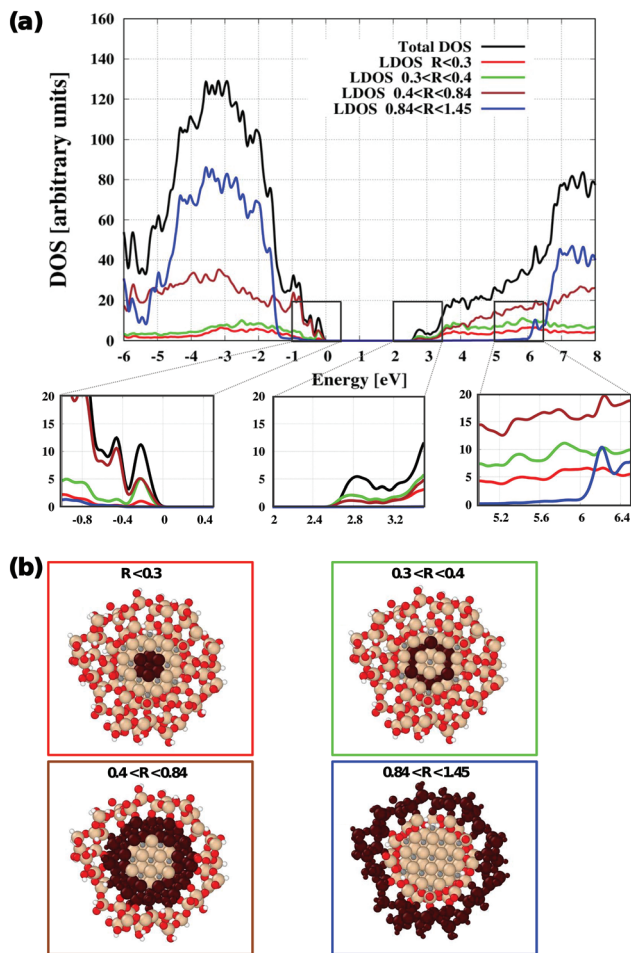


Fig. 2 (a) DOS of our computational model of SiC/SiO_x core/shell NW; the upper panel (a) shows both the total Density of States (black line) and the local DOS (LDOS) obtained by projecting the DOS onto the atoms belonging to different radial shells; the three middle panels report zooms of the top (bottom) region of the valence band (conduction band); (b) NW radial shells (represented in dark brown) on which the DOS projections are performed.

intermediate between the SiC core and the SiO_x shell (*i.e.* VBM reminds that of SiO_x, whereas the CBM resembles that of SiC).

3.3 Simulations of XANES spectra

XANES experimental spectra were reproduced from *ab initio* simulations using density functional theory. To perform these calculations we used the XSpectra computer code,⁶⁸ which relies on the Quantum ESPRESSO suite.⁶⁹ The input of the approach implemented in XSpectra is basically the ground state electron density. K-edge absorption spectra are computed upon the knowledge of the electron density *via* the continued fraction method and the Lanczos chain algorithm, tailored to be used with pseudopotentials.⁶⁸ The convenience of using this approach is mainly due to its low computational cost, as it is based on one only self-consistent DFT run and does not require the explicit calculation of the empty states. The draw-

back of this method is that one loses useful pieces of information (*e.g.* symmetry) on the final transition states.

The absorption of X-ray photons results typically in a core-hole, while the electron is promoted to an empty state. To enable the pseudopotential approach, in which core electrons are typically frozen, to describe this mechanism, one needs to perform DFT simulations with pseudopotentials carrying an inner hole, typically in the 1s state for K-edge absorption spectroscopy. Ultra-soft core-hole pseudopotentials, used to perform XANES simulations, for treating the ionic core-valence electron interactions in C, O, and Si atoms can be found in the Quantum ESPRESSO database.⁷⁰ The all-electron wavefunction is then recovered *via* the projector augmented wave (PAW) formalism.⁷¹ In particular, for the C pseudopotential we used two projectors on the s and p atomic states, while for Si and O we used two projectors for the s and p states and one for the d state. After convergence tests (details are reported in ESI (sub section 2†)), DFT simulations have been carried out using a kinetic energy cut-off equal to 544 eV for wavefunctions and four times as much for the electron density. A $1 \times 1 \times 2$ *k*-point sampling of the Brillouin zone was sufficient to obtain converged energy and DOS below chemical accuracy.

XANES spectra are calculated in the dipole approximation, thus due to symmetry K-edge spectroscopy probes only the transitions from 1s to np or s/p-hybridized orbitals. Spectra simulations were performed using a $1 \times 1 \times 4$ *k*-point grid for sampling the Brillouin zone. Three different polarization vectors of the incident light were considered, that is one along the NW symmetry axis (*z*-axis) and two perpendicular to it (*x* and *y* directions). A dependence of the spectral signals on polarization directions is expected in presence of radial anisotropy, *e.g.* for defected NWs. In all XANES simulations spectral lineshapes have been broadened by a convolution with a Lorentzian function having the half width at half maximum constant at all energies and equal to 0.8 eV.

Numerical tests were carried out in the case of SiC crystals and of SiC NW with –OH terminations. Good agreement of our calculations with experimental measurements and similar computer simulations^{52,54} on these structures was found using the above-mentioned computational parameters. These encouraging results on SiC NW led us to use the model of SiC/SiO_x core/shell NW previously introduced to interpret our experimental absorption data. More computational details on XANES simulations are reported in ESI (sub section 2.1†).

4 Results and discussion

4.1 Silicon K-edge XANES spectra

Before investigating the Si, O, and C K-edge absorption lineshape of the SiC/SiO_x core/shell NW, we start our analysis by simulating the electronic and optical properties of the OH-terminated SiC core. This configuration represents a simplified model of the SiC core NW, which can be experimentally obtained by completely etching away the silica outer shell (HF-etched SiC NWs). In Fig. 3 we report the theoretical Si K-edge

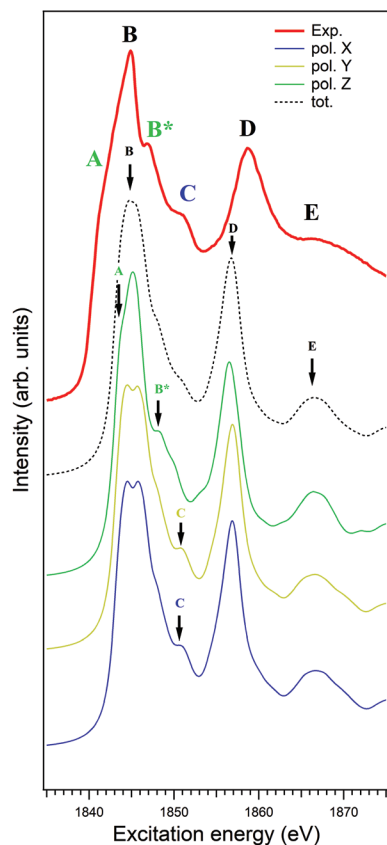


Fig. 3 Experimental Si K-edge XANES spectrum of HF-etched SiC core nanowires (red), in comparison with theoretical XANES spectra of (dashed line) an OH-terminated SiC core NW. Blue, khaki, and green curves show the spectra originating from *x*-, *y*-, and *z*-polarized electric fields, respectively.

spectrum (black dashed line) in comparison to our experimental data (red line). Furthermore, in this figure we report the spectral contribution to the total lineshape of the light polarized along the three orthogonal cartesian directions: the blue, khaki, and green curves show the spectra originating from *x*-, *y*-, and *z*-polarized electric fields, respectively. The total spectrum is obtained by averaging along the three polarization directions. The experimental lineshape of the Si K-edge exhibits five features A–E that are typically observed for 3C-SiC thin films^{72–74} and HF-etched 3C-SiC NWs.^{52,75} Differently to previous reports, we observe an additional feature B* at 1847 eV that becomes only visible when the freshly etched sample was immediately inserted into the UHV chamber. Longer exposure to air leads to the disappearance of this feature (see Fig. S20a of ESI†), suggesting that it originates from the SiC/SiO_x interface (*i.e.*, before any re-oxidation appears). We notice that the simulated spectra are in good agreement with experiments, and they reproduce all the peaks denoted in Fig. 3. It is noteworthy that the shoulder A (at 1841.5 eV in the experimental spectrum) strongly depends on the polarization direction: it is well separated from the main peak B for *x*- and *y*-polarized electric fields, whereas it decreases in intensity and

appears as shoulder for *z* polarization direction. Moreover, peak B* is more pronounced in the spectrum with the *z*-polarized electric field. Overall, the theoretical spectral lineshape in the *z* polarization direction agrees well with the experimental one.

The peaks denoted as B, D, and E in Fig. 3 correspond to transitions from the Si 1s orbital to hybridized states from both Si and C. In particular, the main resonance (B peak at 1845 eV), and the peaks D and E at 1849 and 1867 eV, respectively, can be attributed to the transition of Si 1s electrons to orbitals that have lost their atomic character and arise by mixing hybridized 2s and 2p orbitals of C and hybridized 3s, 3p, and 3d orbitals of Si.⁷⁵ This combination is due to the overlap between 3s, 3p, and 3d orbitals from Si and 2s and 2p orbitals from C, which are degenerate as one can clearly see in Fig. S6 of the ESI.†

Theoretical interpretation of the Si K-edge absorption spectra has been carried out by comparison with our experimental measurements also in the SiC/SiO_x core/shell NW. Both simulated and experimental Si K-edge spectra, along with the contributions resolved in the polarization directions of the incident electric field, are reported in Fig. 4. Si atoms in different chemical environments are present in the SiC core as well as in the SiO_x outer shell. Thus, theoretical spectra were obtained by creating core-holes in two different locations of the NW. In Fig. 4 the K-edge spectrum obtained *via* photon absorption by Si atoms within the outer shell of the NW is labeled as Si_h^{shell} (black dashed line in the upper part of the figure), while the spectrum labeled as Si_h^{core} (black dashed line in the lower part of the figure) has been generated by creating the core-hole in the Si atoms within the NW SiC core. The Si_h^{shell} spectrum reports the features typical of silica, that is a single main peak C' (see also Fig. S20 of ESI†).⁶⁸ At variance, the Si_h^{core} absorption spectrum is similar to that one obtained in the SiC + OH NW (see Fig. 3). The pre-edge peak labeled as A' at 1842 eV in the experimental spectrum in Fig. 4 can be unambiguously attributed to a contribution stemming from the SiC core, since it cannot be found in the SiO_x NWs without SiC core (see Fig. S20b of ESI†). In general, the spectral lineshape can be rationalized as the convolution of the signals obtained by creating the core-hole in different locations in the SiC core and in the SiO_x outer shell. Nevertheless, a much stronger contribution of the Si_h^{shell} is visible. Taking into account this feature, which can be understood by considering that the TEY experimental technique probes mainly the sample's surface, good agreement is obtained between experimental (red line) and theoretical spectral lineshape. Similar to Fig. 3, the shoulder B' at 1845.5 eV is strongly dependent on the polarization direction (*i.e.*, more pronounced for *x*- and *z*-polarized electric fields), and the spectral lineshape of the experimental data is mainly dominated by the theoretical one of the Si_h^{shell} in *z* polarization direction. We notice that the main peak C' in Fig. 4 (at 1847 eV) is largely due to electron transitions from Si 1s to a combination of Si 3p, 3d orbitals, due to the selection rules (see Fig. S6 of ESI† for a symmetry-resolved representation of the DOS).

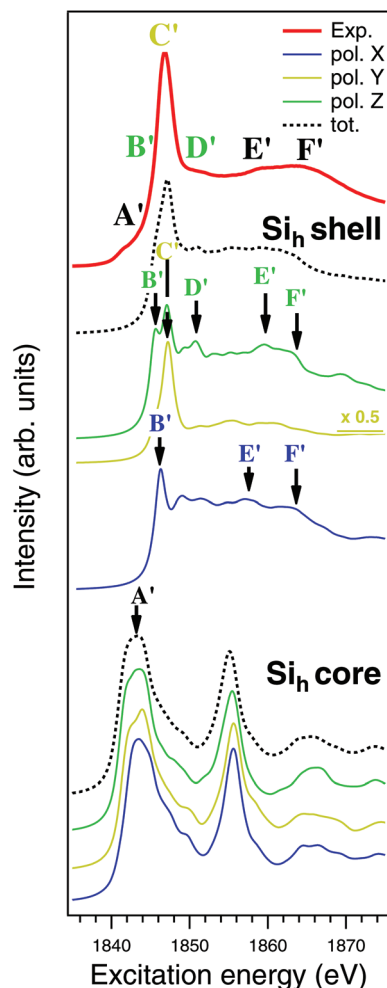


Fig. 4 Experimental Si K-edge XANES spectrum of as-grown SiC/SiO_x core/shell NWs (red), in comparison with theoretical XANES spectra (dashed line) of a SiC/SiO_x core/shell NW (without carbon defects). Si_h^{shell} and Si_h^{core} represent the absorption spectra obtained by creating a core-hole in a silicon atom within the SiO_x shell and the SiC core, respectively. Blue, khaki, and green curves show the spectra originating from x-, y-, and z-polarized electric fields, respectively.

4.2 Oxygen K-edge XANES spectra

The comparison between the theoretical O K-edge XANES spectra (black dashed lines) obtained in our SiC core + OH model NW and the experimental O K-edge XANES spectrum of HF-etched SiC core NWs (red line) is reported in Fig. 5. In all simulated spectra blue, khaki, and green curves show the features originating from x-, y-, and z-polarized electric fields, respectively. The two theoretical spectra (black dashed lines) in the upper and middle parts of Fig. 5, labeled as -Si-O_hH and -C-O_hH, correspond to spectral features originating from different locations of the excited O atom on the NW surface: on the one hand, O binds to Si (-Si-O_hH), and on the other hand to C (-C-O_hH). We notice that good agreement between experimental and theoretical data is found, with the main features fully described by *ab initio* simulations using our NW model. In particular, the main peak 3 at 536 eV is present in

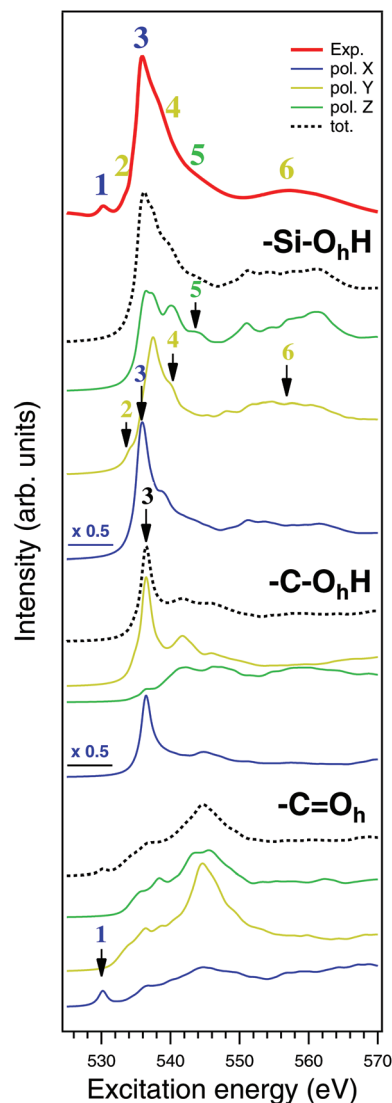


Fig. 5 Experimental O K-edge XANES spectrum of HF-etched SiC core nanowires (red line), in comparison with theoretical spectra of an OH-terminated SiC core NW (black dashed lines). The three theoretical spectra with the relevant polarizations (blue, khaki, and green curves, respectively) refer to the -OH radicals attached to a silicon atom (upper theoretical spectrum), to a carbon atom (middle theoretical spectrum), and to unsaturated oxygen (lower theoretical spectrum).

both simulated spectra -Si-O_hH (x-polarization) and -C-O_hH (x- and y-polarization), whereas the shoulder 2 at 534 eV and the features 4, 5 and 6 (at 540, 544 and 557 eV) are only reproduced by the -Si-O_hH simulated spectra (contributions from y- and z-polarization).

Finally, in the lower part of Fig. 5 we report the spectrum, labeled as -C=O_h, simulating the presence of unsaturated oxocarbons (carbonyl groups) on the SiC NW surface. The line-shape, originating from O atoms that form double covalent bonds with the adjacent carbon atom, explains the pre-edge peak at 530 eV denoted by 1 in the experimental spectrum (red line). The peaks in all spectra can be described in terms of

electron excitations from the O 1s orbital to a mixing between hybridized 2s, 2p orbitals of C or 3s, 3p orbitals of Si and the 2s, 2p orbitals of O.

In Fig. 6 we report the comparison between experimental (red line) and simulated (black dashed line) O K-edge XANES spectra of the SiC/SiO_x core/shell NW. In addition, the lower part of Fig. 6 shows the simulated spectra of -C=O_h carbonyl groups on the NWs' silica surface. The main features 2'–6' of the experimental spectrum are all clearly visible in the theoretical spectrum without carbon defects, when the different polarization contributions are summed up (blue, khaki, and green curves show the spectra originating from x-, y-, and z-polarized electric fields, respectively). This finding further supports our computational model of the SiC/SiO_x core/shell NW. In particular, the main broad peak in the energy range 535–540 eV is split into two separate contributions, namely into peak 2' at 535 eV originating from the y- (khaki line) and z- (green line) polarization directions of the incident light, whereas peak 3' at 537 eV originates from the x- (blue line) polarization direction. Moreover, the shoulder 4' visible at 541 eV is recovered by convolution of features present in all the

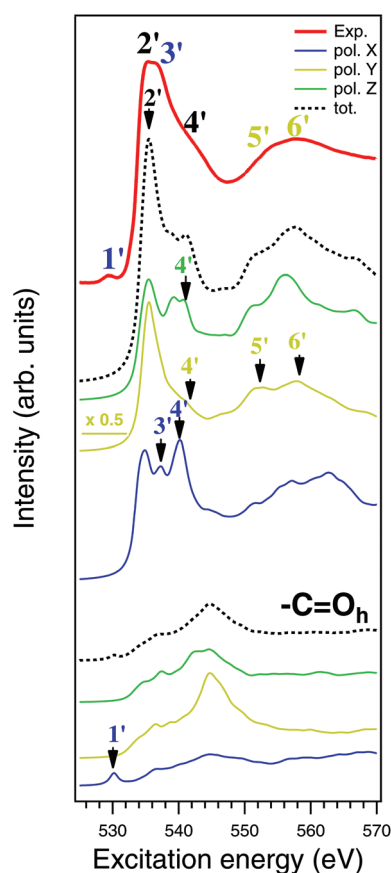


Fig. 6 Experimental O K-edge XANES spectrum of as-grown SiC/SiO_x core/shell NWs (red), in comparison with theoretical spectra (black dashed line) of a SiC/SiO_x core/shell NW (without carbon defects). In the lower panel we report again the spectral features originating from unsaturated oxygen. Blue, khaki, and green curves show the spectra originating from x-, y-, and z-polarized electric fields, respectively.

polarization directions x, y and z. The broad features 5' and 6' found in the experimental spectrum at 552.5 and 558 eV, respectively, are present in all the three polarization directions of the simulated spectra, but its lineshape can be mainly understood by looking at the lineshape of the y-polarization contribution (khaki curve).

A similar experimental lineshape of the O K-edge XANES spectrum, *i.e.*, a relatively broad resonance between 535–550 eV, but no pre-edge peak 1' was previously observed in a SiO₂ thin film (4 nm) thermally oxidized on SiC⁵⁰ as well as in thermally oxidized Si NWs.⁷⁶ At variance, our SiO_x NWs (grown without SiC core) exhibit the same pre-edge peak at 530 eV (see Fig. S21 of ESI†) than the SiC/SiO_x core/shell NWs. It is noteworthy that a different view about the origin of the pre-edge peak 1/1' in O K-edge XANES spectra of SiO_x-based materials exists in the literature. For instance, in SiO_x films grown on SiC it has been assumed that it originates from defect states such as O vacancies at the SiO_x/SiC interface.⁴⁸ Furthermore, a similar pre-edge peak has been observed in quartz,⁷⁷ which has been assigned to the transition from the O 1s electron to the π^* orbital states of O₂ molecules that are induced by radiation damage from the X-ray beam with high incident flux.⁷⁸ At odds with this theory, we could observe the pre-edge peak even during acquisition at very low flux (at BEAR beamline, *i.f.* $<1 \times 10^9$ photons per s, see Fig. S21 of ESI†), thus, we can exclude any effects caused by radiation damage. As in the case of O K-edge spectrum of HF-etched SiC core NW (see Fig. 5) the pre-edge peak 1' located at 530 eV in Fig. 6 can be safely attributed to double bonded oxygen, *e.g.* belonging to carbonyl groups (see simulated spectra of -C=O_h in the lower part of Fig. 6). To further confirm this theory, we measured the O K-edge XANES spectrum of NWs after surface functionalization with an organic molecule containing carboxyl groups (see Fig. S21 of ESI†). Indeed, we found an increase of the pre-edge peak, supporting the idea that it originates from carbon-containing (functional) groups such as carbonyl and/or carboxyl groups.⁷⁹

4.3 Carbon K-edge XANES spectra

The comparison between the C K-edge XANES simulated spectrum of OH-terminated SiC core NW (black dashed line) and the experimental spectrum of HF-etched SiC core NWs (red line) is reported in Fig. 7. The color code for the three orthogonal polarization directions of the incident X-ray photon beam is the same as for the previously discussed Si and O K-edge XANES spectra. To consider contributions stemming from the SiC/SiO_x interface, we simulated a typical carbon-related defect (lower part of Fig. 7). In principle, this structure is created when a Si atom in SiO_x is substituted by a C atom, and resembles a C atom in sp³ configuration corresponding to SiO_xC_y species (*i.e.*, silicon oxycarbides indicated as grey-shaded area in the structure in Fig. 7), which are typically resistant to HF etching. We notice that the clusters represented in Fig. 7 and 8 were cut out of the full simulation cell with the only aim of zooming the several chemically different local environments in which carbon atoms can be found in their

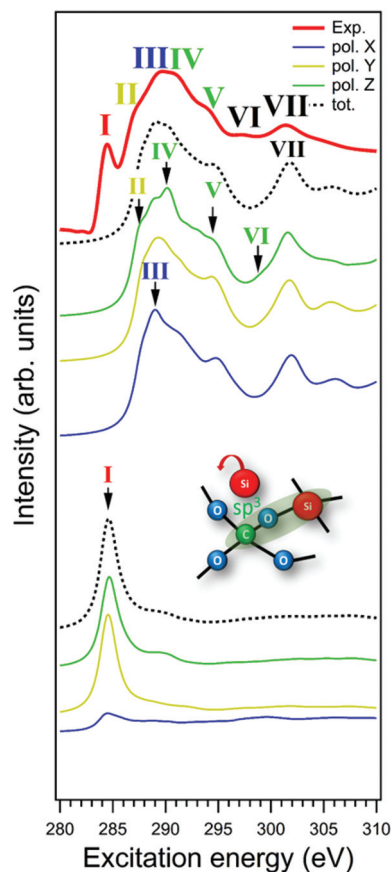


Fig. 7 Experimental C K-edge XANES spectrum of HF-etched SiC core NWs (in red), in comparison with theoretical spectra (black dashed line) of an OH-terminated SiC core NW. The simulated spectra in the lower panel refer to residual silicon oxycarbides (grey-shaded area in the structure) that remain as residuals at the SiC surface after etching the SiO_x shell. Blue, khaki, and green curves show the spectra originating from x-, y-, and z-polarized electric fields, respectively.

binding to other atoms. These realistic binding conditions of the carbon atoms within the different clusters, which are embedded in the NW, are then used to disentangle the spectral contributions of the single defects to the total lineshape. Nevertheless, XANES spectra are calculated using the full simulation cell.

Our experimental lineshape of the C K-edge XANES spectrum is in good agreement with previous reports for 3C-SiC thin films^{80–82} and HF-etched 3C-SiC NWs.^{52,75} Apart from the first feature I located at 284.5 eV, the theoretical spectrum (without defects) reproduces well the experimental shape. In our model of SiC core NW with –OH termination, C atoms that are not on the surface form sp³ hybridized orbitals bonding with Si atoms. We assign the spectral features in the near edge region (energy range between 285 and 300 eV) to the dipole transitions from the C 1s orbitals to σ*-character bands formed by the sp³-hybridized orbitals of C, tetrahedrally coordinated with four Si atoms.⁵² At variance, the pre-edge peak I can be attributed to the transition from the (sp³) C 1s atoms at the SiO_x/SiC interface (see lower panel in Fig. 7), where a

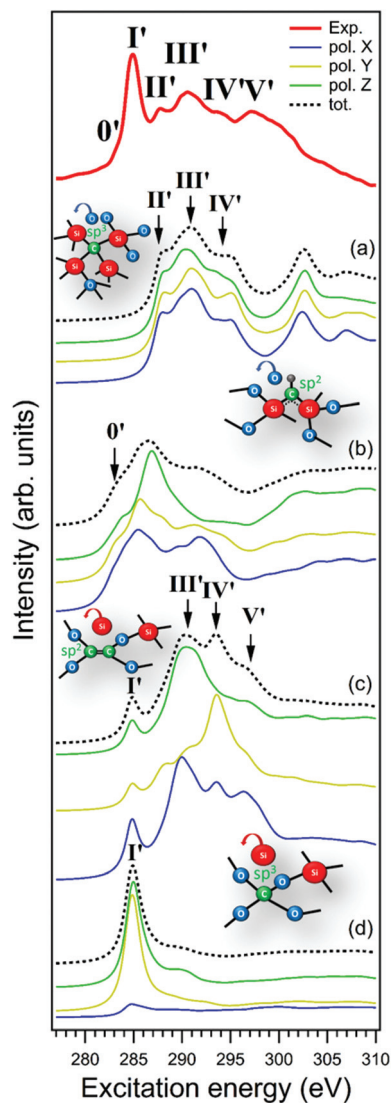


Fig. 8 Experimental C K-edge XANES spectrum of as-grown SiC/SiO_x core/shell NWs (red), compared to theoretical XANES spectra (black dashed line) of SiC/SiO_x core/shell NW. The four spectra reported in this figure are obtained by including several different carbon defects in the shell, which are represented close to each corresponding theoretical spectrum. Spectra originating from x-, y-, and z-polarized electric fields are reported in blue, khaki, and green, respectively.

layer of silicon oxycarbides is typically formed due to the growth process and conditions and remains as residual thin (0.5–2 nm) layer around the SiC core.³⁶

It is noteworthy, that such a pre-edge peak I has been previously assigned in (HF-etched) 3C-SiC NWs to graphite-like π* states of sp² bonded carbon atoms.⁷⁵ Although we cannot exclude any contributions from C atoms in sp² configuration, our findings strongly suggest that a strong contribution originates from the silicon oxycarbides (in sp³ configuration) present at the SiO_x/SiC interface.

Finally, in Fig. 8 we report the C K-edge XANES theoretical spectra of the SiC/SiO_x core/shell NW (black dashed lines)

compared to our experimental data (red line). Here we report four different simulated spectra corresponding to different chemical environments, and thus different bonding, in which C atoms can be reasonably found.²⁰ Special emphasis was drawn to simulate C atoms not only in sp^3 but also in sp^2 configuration, since additional peaks in the C K-edge XANES spectrum of SiC/SiO_x core/shell NWs have been associated to sp^2 C defects present in or on the silica shell,⁵² similar to the SiC case. The different coordination bonds are represented close to the corresponding XANES spectrum in Fig. 8.

The upper theoretical spectrum in Fig. 8(a) is obtained when an oxygen atom in the SiO_x shell is substituted by a carbon atom, *i.e.*, a sp^3 configuration very similar to that reported in Fig. 7 (upper panel) for the -OH terminated SiC NW. The presence of additional different C defects corresponding to the three lower spectra (b)–(d) in Fig. 8 could be explained by the carbothermal process used in the present study to synthesize the SiC/SiO_x core/shell NWs, which inevitably creates C inclusions/contaminants in the SiO_x shell. The additional defects studied in this work can be divided in two classes, namely substitutional inclusions and surface contaminants. Within the first class belongs the substitution of an oxygen atom in the shell with a -CH group (sp^2 configuration, see Fig. 8(b)), the substitution of a Si atom in the shell with two C atoms forming a double bond (sp^2 configuration, see Fig. 8(c)), and the substitution of a silicon atom in the shell with a four coordinated carbon atom (sp^3 configuration, see Fig. 8(d)), similar to the case in Fig. 7 (lower panel). The second class of defects is characterized by the surface contamination of carboxyl group (the relevant spectrum is reported in the ESI (sub section 2.3†)).

As can be seen, the theoretical spectrum in Fig. 8(a) mainly reproduces the features II'–V' of the experimental spectrum, whereas the shoulder 0' at 283 eV and the main peak I' at 285 eV, respectively, are not present.

However, the theoretical spectrum of the sp^2 configuration (b) in Fig. 8 indeed reproduces the shoulder 0', whereas the sp^2 configuration (c) in Fig. 8 contributes to the main peak I'. The spectrum of the sp^3 configuration in Fig. 8(d) is once again composed by a single main peak which gives a strong contribution to peak I'.

Our detailed theoretical analysis for different configurations of the SiC/SiO_x core/shell NWs, while not claiming to be exhaustive, demonstrates that the XANES experimental signals are due to a variety of defects and that spectral lineshapes crucially depend on the local bonding environment of the excited atom, which must be carefully assessed.

5 Conclusions

SiC/SiO_x core/shell NWs are very promising systems in a variety of applications, ranging from energy harvesting to developing novel methods for cancer therapy and diagnosis. To optimize these procedures, an accurate characterization of the electronic and optical properties of these novel structures *via* a synergic

experimental and computational study is necessary. To the best of our knowledge this work was aimed at developing for the first time a realistic model of SiC/SiO_x core/shell NWs, relying on information gained both at experimental and theoretical level.

SiC/SiO_x core/shell NWs were synthesized *via* a low-cost carbothermal method. Structural features of these NWs were investigated *via* the acquisition of XANES spectra in TEY mode and their theoretical interpretation from *ab initio* simulations. Our NW model, including defected sites and interfacial boundaries between SiC and SiO_x, reproduces remarkably well the main features of C, Si, and O K-edge XANES spectra of these structures arranged in several configurations and stoichiometry.

Both optical and electronic characteristics, such as the DOS, of these systems are crucially affected by two counteracting effects, that is quantum confinement and surface termination. Quantum confinement, induced by the reduced dimensionality of the wire with respect to bulk SiC, results into the modification of the NWs band structure from indirect to direct band gap, with a VBM to CBM distance inversely dependent on wire diameter. Surface passivation of the dangling bonds affects both the NW boundaries and the interfacial region. We devised the presence of a variety of defects, such as substitutional C, and different chemical coordination to obtain an overall good agreement between simulated and experimental XANES spectral lineshapes at the Si, O, and C absorption K-edge. This study demonstrates the crucial importance of defective sites in affecting the electronic characteristics of SiC NWs, so to avoid unintentional doping that hinders the development of high-performance SiC-based field-effect transistors.

Finally, the realistic model of SiC/SiO_x core/shell NWs proposed in this combined experimental and theoretical study, being able to deliver an accurate interpretation of the recorded XANES spectra, demonstrates to be a valuable tool towards the optimal design and application of these nanosystems in real devices.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors would like to thank Mr G. Attolini and Dr M. Bosi for the growth of the SiC/SiO_x core/shell nanowires. Dr K. Koshmak is gratefully acknowledged for the support and stimulating discussions concerning the XANES measurements at ELETTRA. M. T. gratefully acknowledges the support by a Feodor-Lynen-Fellowship of the Alexander v. Humboldt foundation, Bonn (Germany). This study was supported by the CARITRO Foundation, project FoXIR (Progetti di ricerca scientifica svolti da giovani ricercatori, 2015). N. M. P. is supported by the European Commission under the Graphene Flagship

Core2 no. 785219 (WP14 “Polymer Composites”), FET Proactive “Neurofibres” grant no. 732344 and by the Italian Ministry of Education, University and Research (MIUR) under the ‘Departments of Excellence’ grant L.232/2016. Access to computing and storage facilities owned by parties and projects contributing to the National Grid Infrastructure MetaCentrum provided under the program “Projects of Large Research, Development, and Innovations Infrastructures” (CESNET LM2015042), is greatly appreciated (<https://www.metacentrum.cz/en/>). Finally, the authors gratefully acknowledge the Gauss Centre for Supercomputing for funding this project by providing computing time on the GCS Supercomputer JUQUEEN at Jülich Supercomputing Centre (JSC).⁸³ Furthermore, the authors acknowledge FBK for providing unlimited access to the KORE computing facility.

References

- 1 P. Reinke, *Inorganic Nanostructures*, Wiley-VCH Verlag & Co. KGaA, Weinheim, Germany, 2012.
- 2 P. C. Spruijtenburg, J. Ridderbos, F. Mueller, A. W. Leenstra, M. Brauns, A. A. I. Aarnink, W. G. van der Wiel and F. A. Zwanenburg, *Appl. Phys. Lett.*, 2013, **102**, 192105.
- 3 Y. Ji, Y. Zhai, H. Yang, J. Liu, W. Shao, J. Xu, W. Li and K. Chen, *Nanoscale*, 2017, **9**, 16038–16045.
- 4 T. D. Ladd, F. Jelezko, R. Laflamme, Y. Nakamura, C. Monroe and J. L. O’Brien, *Nature*, 2010, **464**, 45–53.
- 5 S. Barth, F. Hernandez-Ramirez, J. D. Holmes and A. Romano-Rodriguez, *Prog. Mater. Sci.*, 2010, **55**, 563–627.
- 6 J. Zhong, H. Zhang, X. Sun and S.-T. Lee, *Adv. Mater.*, 2014, **26**, 7786–7806.
- 7 N. Fukata, T. Subramani, W. Jevasuwan, M. Dutta and Y. Bando, *Small*, 2017, **13**, 1701713.
- 8 M. Shao, L. Cheng, X. Zhang, D. D. D. Ma and S.-T. Lee, *J. Am. Chem. Soc.*, 2009, **131**, 17738–17739.
- 9 K.-Q. Peng and S.-T. Lee, *Adv. Mater.*, 2011, **23**, 198–215.
- 10 T. J. Kempa, R. W. Day, S.-K. Kim, H.-G. Park and C. M. Lieber, *Energy Environ. Sci.*, 2013, **6**, 719–733.
- 11 K. Peng, J. Jie, W. Zhang and S.-T. Lee, *Appl. Phys. Lett.*, 2008, **93**, 033105.
- 12 S. Sim, P. Oh, S. Park and J. Cho, *Adv. Mater.*, 2013, **25**, 4498–4503.
- 13 G. Zheng, F. Patolsky, Y. Cui, W. U. Wang and C. M. Lieber, *Nat. Biotechnol.*, 2005, **23**, 1294–1301.
- 14 K.-I. Chen, B.-R. Li and Y.-T. Chen, *Nano Today*, 2011, **6**, 131–154.
- 15 J. L. Coffey, *Semiconducting Silicon Nanowires for Biomedical Applications*, Elsevier Science, Cambridge, 2014.
- 16 C. R. Eddy Jr. and D. K. Gaskill, *Science*, 2009, **324**, 1398–1400.
- 17 S. Taioli, G. Garberoglio, S. Simonucci, S. a. Beccara, L. Aversa, M. Nardi, R. Verucchi, S. Iannotta, M. Dapor and D. Alfè, *J. Chem. Phys.*, 2013, **138**, 044701.
- 18 R. Verucchi, L. Aversa, M. V. Nardi, S. Taioli, S. A. Beccara, D. Alfè, L. Nasi, F. Rossi, G. Salviati and S. Iannotta, *J. Am. Chem. Soc.*, 2012, **134**, 17400–17403.
- 19 L. Aversa, S. Taioli, M. V. Nardi, R. Tatti, R. Verucchi and S. Iannotta, *Front. Mater.*, 2015, **2**, 46.
- 20 F. Devynck, A. Alkauskas, P. Broqvist and A. Pasquarello, *AIP Conf. Proc.*, 2010, **1199**, 108–109.
- 21 X. Shen and S. T. Pantelides, *Appl. Phys. Lett.*, 2011, **98**, 053507.
- 22 K. Zekentes and K. Rogdakis, *J. Phys. D: Appl. Phys.*, 2011, **44**, 133001.
- 23 L. Latu-Romain and M. Ollivier, *J. Phys. D: Appl. Phys.*, 2014, **47**, 203001.
- 24 J. Prakash, R. Venugopalan, B. M. Tripathi, S. K. Ghosh, J. K. Chakravarty and A. K. Tyagi, *Prog. Solid State Chem.*, 2015, **43**, 98–122.
- 25 Y. Zhang, X. Han, K. Zheng, Z. Zhang, X. Zhang, J. Fu, Y. Ji, Y. Hao, X. Guo and Z. Wang, *Adv. Funct. Mater.*, 2007, **17**, 3435–3440.
- 26 P. Hu, S. Dong, X. Zhang, K. Gui, G. Chen and Z. Hu, *Sci. Rep.*, 2017, **7**, 3011.
- 27 R. Wu, K. Zhou, Z. Yang, X. Qian, J. Wei, L. Liu, Y. Huang, L. Kong and L. Wang, *CrystEngComm*, 2013, **15**, 570–576.
- 28 M. Han, X. Yin, W. Duan, S. Ren, L. Zhang and L. Cheng, *J. Eur. Ceram. Soc.*, 2016, **36**, 2695–2703.
- 29 W. M. Zhou, F. Fang, Z. Y. Hou, L. J. Yan and Y. F. Zhang, *IEEE Electron Device Lett.*, 2006, **27**, 463–465.
- 30 S. Z. Deng, Z. B. Li, W. L. Wang, N. S. Xu, J. Zhou, X. G. Zheng, H. T. Xu, J. Chen and J. C. She, *Appl. Phys. Lett.*, 2006, **89**, 023118.
- 31 M. Negri, S. C. Dhanabalan, G. Attolini, P. Lagonegro, M. Campanini, M. Bosi, F. Fabbri and G. Salviati, *CrystEngComm*, 2015, **17**, 1258–1263.
- 32 Z. J. Li, H. Y. Yu, G. Y. Song, J. Zhao, H. Zhang, M. Zhang, A. L. Meng and Q. D. Li, *Phys. Chem. Chem. Phys.*, 2017, **19**, 3948–3954.
- 33 X. Li, J. Huang, J. Lu, Z. Feng, J. Luo and M. Xue, *J. Mater. Sci.*, 2017, **52**, 3344–3352.
- 34 Y. Ryu, Y. Tak and K. Yong, *Nanotechnology*, 2005, **16**, S370–S374.
- 35 S. Carapezzi, A. Castaldini, F. Fabbri, F. Rossi, M. Negri, G. Salviati and A. Cavallini, *J. Mater. Chem. C*, 2016, **4**, 8226–8234.
- 36 F. Fabbri, F. Rossi, G. Attolini, G. Salviati, S. Iannotta, L. Aversa, R. Verucchi, M. Nardi, N. Fukata, B. Dierre and T. Sekiguchi, *Nanotechnology*, 2010, **21**, 345702.
- 37 M. Zhang, J. Zhao, Z. Li, H. Yu, Y. Wang, A. Meng and Q. Li, *J. Solid State Chem.*, 2016, **243**, 247–252.
- 38 J. J. Niu, J. N. Wang and Q. F. Xu, *Langmuir*, 2008, **24**, 6918–6923.
- 39 F. Fabbri, F. Rossi, M. Melucci, I. Manet, G. Attolini, L. Favaretto, M. Zambianchi and G. Salviati, *Nanoscale Res. Lett.*, 2012, **7**, 680.
- 40 F. Rossi, E. Bedogni, F. Bigi, T. Rimoldi, L. Cristofolini, S. Pinelli, R. Alinovi, M. Negri, S. C. Dhanabalan, G. Attolini, F. Fabbri, M. Goldoni, A. Mutti, G. Benecchi, C. Ghetti, S. Iannotta and G. Salviati, *Sci. Rep.*, 2015, **5**, 7606.

- 41 R. Tatti, M. Timpel, M. V. Nardi, F. Fabbri, F. Rossi, L. Pasquardini, A. Chiasera, L. Aversa, K. Koshmak, A. Giglia, L. Pasquali, T. Rimoldi, L. Cristofolini, G. Attolini, S. Varas, S. Iannotta, R. Verucchi and G. Salviati, *Mol. Syst. Des. Eng.*, 2017, **2**, 165–172.
- 42 V. Presser and K. G. Nickel, *Crit. Rev. Solid State Mater. Sci.*, 2008, **33**, 1–99.
- 43 V. V. Afanasev, M. Bassler, G. Pensl and M. Schulz, *Phys. Status Solidi A*, 1997, **162**, 321–337.
- 44 S. Dhar, L. C. Feldman, S. Wang, T. Isaacs-Smith and J. R. Williams, *J. Appl. Phys.*, 2005, **98**, 014902.
- 45 K. C. Chang, J. Bentley and L. M. Porter, *J. Electron. Mater.*, 2003, **32**, 464–469.
- 46 Y. Hijikata, H. Yaguchi, M. Yoshikawa and S. Yoshida, *Appl. Surf. Sci.*, 2001, **184**, 161–166.
- 47 P. Soukiassian and F. Amy, *J. Electron Spectrosc. Relat. Phenom.*, 2005, **144–147**, 783–788.
- 48 D.-K. Kim, K.-S. Jeong, Y.-S. Kang, H.-K. Kang, S. W. Cho, S.-O. Kim, D. Suh, S. Kim and M.-H. Cho, *Sci. Rep.*, 2016, **6**, 34945.
- 49 C. McGuinness, D. Fu, J. E. Downes, K. E. Smith, G. Hughes and J. Roche, *J. Appl. Phys.*, 2003, **94**, 3919–3922.
- 50 M. Tallarida, R. Sohal and D. Schmeisser, *Superlattices Microstruct.*, 2006, **40**, 393–398.
- 51 R. E. Medjo, B. T. Sendja, J. M. Mane and P. O. Ateba, *Phys. Scr.*, 2009, **80**, 055602.
- 52 L. Liu, Y. M. Yiu, T. K. Sham, L. Zhang and Y. Zhang, *J. Phys. Chem. C*, 2010, **114**, 6966–6975.
- 53 A. Laref, N. Alshammari, S. Laref and S. J. Luo, *Dalton Trans.*, 2014, **43**, 5505–5515.
- 54 E. Rosso and R. Baierle, *Chem. Phys. Lett.*, 2013, **568–569**, 140–145.
- 55 Z. Wang, M. Zhao, T. He, H. Zhang, X. Zhang, Z. Xi, S. Yan, X. Liu and Y. Xia, *J. Phys. Chem. C*, 2009, **113**, 12731–12735.
- 56 R. Rurali, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2005, **71**, 205405.
- 57 W. Li, J. Zhao and D. Wang, *Solid State Commun.*, 2015, **205**, 28–32.
- 58 M. Vörös, A. Gali, E. Kaxiras, T. Frauenheim and J. M. Knaup, *Phys. Status Solidi B*, 2012, **249**, 360–367.
- 59 M. Vörös, P. Deak, T. Frauenheim and A. Gali, *Appl. Phys. Lett.*, 2010, **96**, 051909.
- 60 D. Beke, T. Z. Jánosi, B. Somogyi, D. A. Major, Z. Szekrényes, J. Erostyák, K. Kamarás and A. Gali, *J. Phys. Chem. C*, 2016, **120**, 685–691.
- 61 B. Aradi, B. Hourahine and T. Frauenheim, *J. Phys. Chem.*, 2007, **111**, 5678–5684.
- 62 J. Frenzel, A. F. Oliveira, N. Jardillier, T. Heine, G. Seifert, *Semi-relativistic, self-consistent charge Slater-Koster tables for density functional based tight-binding (DFTB) for materials science simulations*, TU-Dresden, 2004–2009.
- 63 A. Cacchioli, F. Ravanetti, R. Alinovi, S. Pinelli, F. Rossi, M. Negri, E. Bedogni, M. Campanini, M. Galetti, M. Goldoni, P. Lagonegro, R. Alfieri, F. Bigi and G. Salviati, *Nano Lett.*, 2014, **14**, 4368–4375.
- 64 Y. Goldberg, M. E. Levinshstein and S. L. Rumyantsev, *Properties of Advanced Semiconductor Materials GaN, AlN, SiC, BN, SiC, SiGe*, John Wiley & Sons, New York, 2001.
- 65 K. Chenoweth, A. C. T. van Duin and W. A. Goddard, *J. Phys. Chem. A*, 2008, **112**, 1040–1053.
- 66 A. D. Kulkarni, D. G. Truhlar, S. Goverapet Srinivasan, A. C. T. van Duin, P. Norman and T. E. Schwartzentruber, *J. Phys. Chem. C*, 2013, **117**, 258–269.
- 67 S. Plimpton, *J. Comput. Phys.*, 1995, **117**, 1–19.
- 68 C. Gougoussis, M. Calandra, A. P. Seitsonen and F. Mauri, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2009, **80**, 075102.
- 69 P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. D. Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, A. Smogunov, P. Umari and R. M. Wentzcovitch, *J. Phys.: Condens. Matter*, 2009, **21**, 395502.
- 70 P. Giannozzi, O. Andreussi, T. Brumme, O. Bunau, M. Buongiorno Nardelli, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, M. Cococcioni, N. Colonna, I. Carnimeo, A. Dal Corso, S. de Gironcoli, P. Delugas, R. A. DiStasio Jr., A. Ferretti, A. Floris, G. Fratesi, G. Fugallo, R. Gebauer, U. Gerstmann, F. Giustino, T. Gorni, J. Jia, M. Kawamura, H.-Y. Ko, A. Kokalj, E. Küçükbenli, M. Lazzeri, M. Marsili, N. Marzari, F. Mauri, N. L. Nguyen, H.-V. Nguyen, A. Otero-de-la-Roza, L. Paulatto, S. Poncé, D. Rocca, R. Sabatini, B. Santra, M. Schlipf, A. P. Seitsonen, A. Smogunov, I. Timrov, T. Thonhauser, P. Umari, N. Vast, X. Wu and S. Baroni, *J. Phys.: Condens. Matter*, 2017, **29**, 465901.
- 71 P. E. Blöchl, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1994, **50**, 17953–17979.
- 72 Y. K. Chang, H. H. Hsieh, W. F. Pong, M.-H. Tsai, K. H. Lee, T. E. Dann, F. Z. Chien, P. K. Tseng, K. L. Tsang, W. K. Su, L. C. Chen, S. L. Wei, K. H. Chen, D. M. Bhusari and Y. F. Chen, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1998, **58**, 9018–9024.
- 73 F. Neri, F. Barreca, E. Fazio, E. Barletta, G. Mondio, S. Trusso, B. Brendebach and H. Modrow, *J. Vac. Sci. Technol., A*, 2007, **25**, 117–125.
- 74 M. Liu, X. Yang, Y. Gao, R. Liu, H. Huang, X. Zhou and T. K. Sham, *J. Eur. Ceram. Soc.*, 2017, **37**, 1253–1259.
- 75 H. Zhang, Y. Xu, J. Zhou, J. Jiao, Y. Chen, H. Wang, C. Liu, Z. Jiang and Z. Wang, *J. Mater. Chem. C*, 2015, **3**, 4416–4423.
- 76 L. Liu and T.-K. Sham, *Small*, 2012, **8**, 2371–2380.
- 77 Y. Wu, H. Fu, A. Roy, P. Song, Y. Lin, O. Kizilkaya and J. Xu, *RSC Adv.*, 2017, **7**, 41812–41818.
- 78 G. S. Henderson, D. R. Neuville and L. Cormier, *Chem. Geol.*, 2009, **259**, 54–62.
- 79 K. Kim, P. Zhu, N. Li, X. Ma and Y. Chen, *Carbon*, 2011, **49**, 1745–1751.

- 80 M. Pedio, A. Giglia, N. Mahne, S. Nannarone, S. Giovannini, C. Cepek, F. Boscherini, R. Carboni, M. Benfatto and S. Della Longa, *Phys. Scr.*, 2005, **T115**, 308–311.
- 81 M. Tallarida, D. Schmeisser, F. Zheng and F. J. Himpsel, *Surf. Sci.*, 2006, **600**, 3879–3883.
- 82 G. Monaco, M. Suman, D. Garoli, M. G. Pelizzo and P. Nicolosi, *J. Electron Spectrosc. Relat. Phenom.*, 2011, **184**, 240–244.
- 83 Jülich Supercomputing Centre, *J. Large-Scale Res. Facil.*, 2015, **1**, A1.

SUPPLEMENTARY INFORMATION

A Novel Combined Experimental and Multiscale Theoretical Approach to Unravel the Structure of SiC/SiO_x Core/shell Nanowires For Their Optimal Design

Tommaso Morresi, Melanie Timpel, Andrea Pedrielli, Giovanni Garberoglio, Roberta Tatti, Roberto Verruchi, Luca Pasquali, Nicola Maria Pugno, Marco Vittorio Nardi and Simone Taioli

This supplementary information reports further computational details and experimental data on the topics developed in the main text of this work, including: modeling of realistic SiC/SiO_x core/shell nanowires (NWs), simulation of XANES spectra based on these topologies, and additional XANES experimental spectra.

1. Computational details on nanowire structural modeling

1.1. Influence of the radius size and of the surface termination on 3C-SiC nanowires

The SiC nanowires (NWs) were obtained by cleaving a cylinder out of a 3C-SiC supercell along the [111] direction, which represents the growth axis in our synthesis process. The first observable that we assess is the band gap of the SiC NW versus the diameter of the wire. In particular, three NWs with diameters of 1.2, 1.8 and 2.6 nm were modeled.

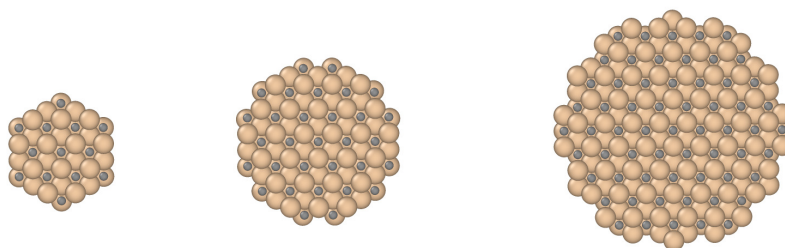


Figure S1: Transverse view of the three SiC core NWs investigated in this work. The NWs diameters are 1.2, 1.8, and 2.6 nm respectively.

To study the electronic properties, we saturated the surface bonds with $-H$ atoms or with $-OH$ (hydroxyl) groups. Structural optimization and electronic band structure simulations were carried out by using the SCC-DFTB method [1]. The total Density of States (DOS) of SiC NWs was computed and compared to 3C-SiC bulk in Fig. S2, to assess the influence of quantum confinement on the electronic properties. We notice that for hydrogenated SiC NWs, the band gap tends to the bulk value, which is 2.3 eV from DFTB simulations (experimentally is reported to be 2.36 eV).

Of course, the DOS of these nanoscale systems dramatically depends on surface termination. Notably we obtain, as reported in Fig. S3, a smaller band gap using $-OH$ instead of $-H$ to passivate the NW surface.

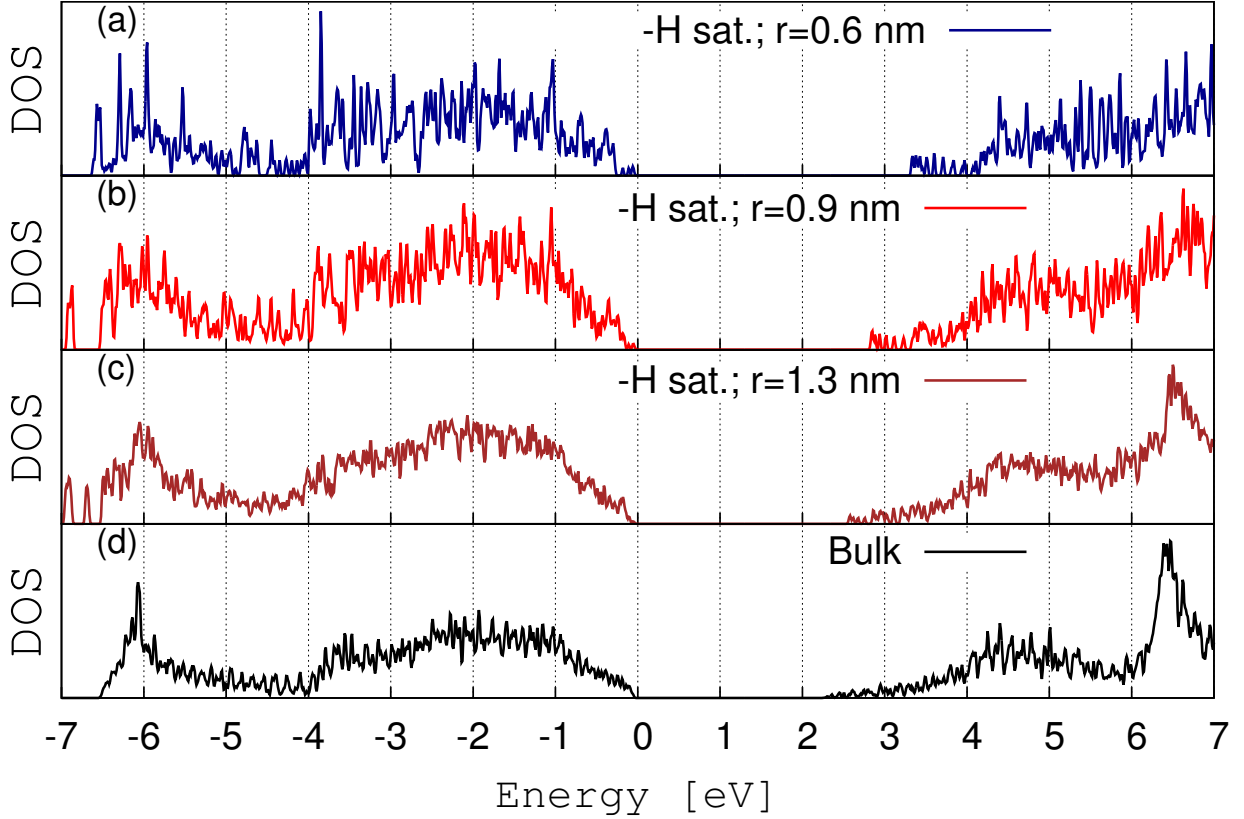


Figure S2: Total DOS of the three different diameter (d) NWs saturated by $-H$ atoms: a) $d=1.2$ nm ; b) $d=1.8$ nm; c) $d=2.6$ nm; d) bulk system

These findings are in agreement with what reported in Ref. [2], where the authors observe a decrease of the band-gap of Si/SiO₂ core-shell quantum dots moving from $-H$ to $-OH$ saturation. To explain this different trend with passivating agents we perform a Mulliken charge distribution analysis. Mulliken charges of C and Si atoms are plotted in Fig. S4 and S5, respectively.

We observe that surface atoms, in particular the carbon atoms in Fig. S4 show a different behaviour for different terminations. This effect influences the electronic properties, such as the band gap, and the Projected Density of States (PDOS). The latter are reported in Figs. S6 and S8. We notice that p orbitals of oxygen atoms contribute to the top of the valence band only in the $-OH$ case, while the lower energy conduction states for both $-H$ and $-OH$ terminations are mainly composed by $p-$ and $d-$ hybridized silicon orbitals. This reduces the band gap in $-OH$ terminated NWs.

In order to further investigate the effect on the electronic properties of passivating with $-H$ and $-OH$ the SiC NWs we performed the calculation of the probability densities of the top of the valence band (VBM) and of the minimum of the conduction band (CBM) in the smallest radius $-H$ and $-OH$ terminated NWs. The plots (isovalue 0.0006 a.u.) of these probability densities (square modulus of the wave functions) are reported in Figs. S10 and S11. We notice that both the VBM (left hand side of Fig. S10) and the CBM (right hand side of S10) are localized in the core of the $-H$ terminated NWs, while for $-OH$ terminated NWs the VBM (left hand side of Fig. S11) is strongly localized on the surface (notably on the oxygen atoms) and the CBM (right hand side of Fig. S11) remains localized in the NW core.

Finally, from our simulations we conclude that two main factors affect the NWs electronic properties: quantum confinement and passivation. These two effects are counteracting: the first broadens the gap, the

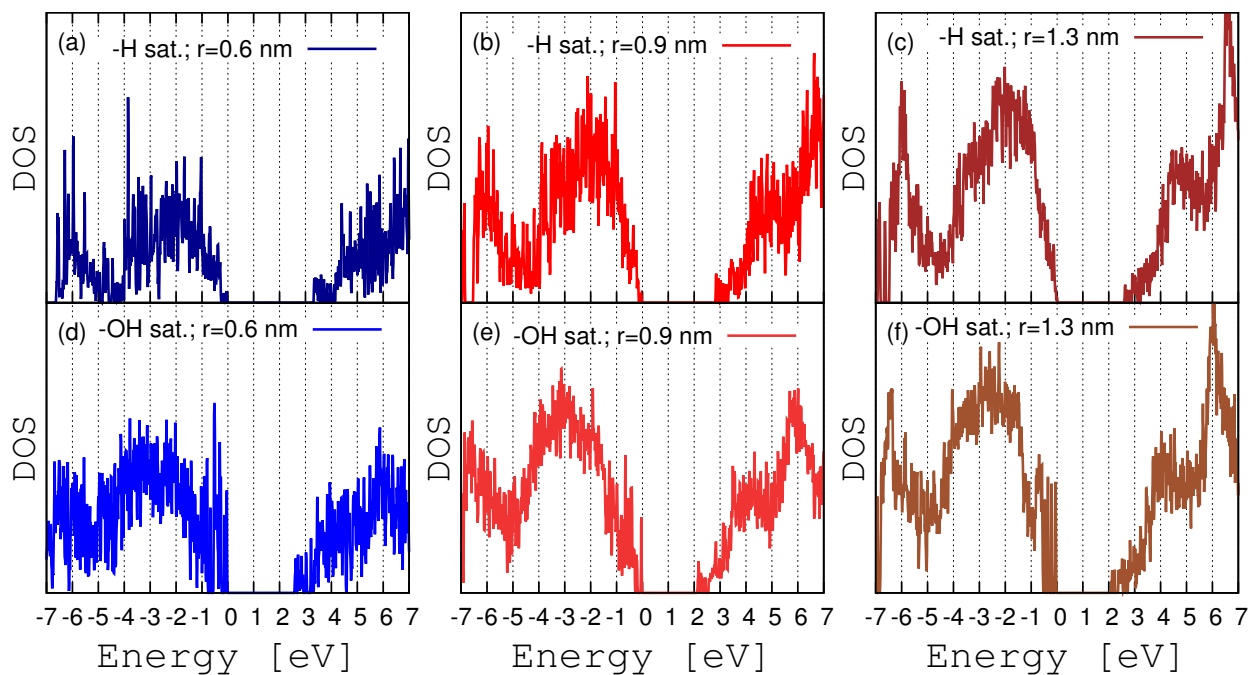


Figure S3: Comparison of the total DOS between $d=1.2$ nm (a,d), $d=1.8$ nm (b,e), and $d=2.6$ nm (c,f) NWs, saturated by H atoms (a,b,c) and by -OH groups (d,e,f).

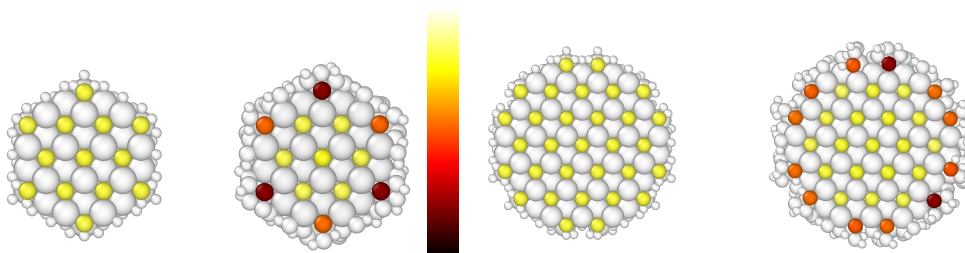


Figure S4: Mulliken charge distribution analysis of carbon atoms (colored atoms) in the SiC NWs with diameters 1.2 (left panel) and 1.8 (right panel) nm. In both figures the nanowire in the left hand side is -H terminated while in the right side is -OH terminated. The charge scale starts from 3.6 (dark) to 4.4 (white).

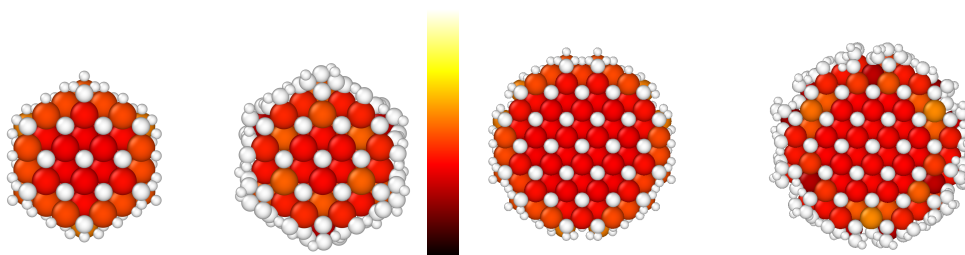


Figure S5: Mulliken charge distribution analysis of silicon atoms (colored atoms) in the SiC NWs with diameters 1.2 (left panel) and 1.8 (right panel) nm. In both figures the nanowire in the left hand side is -H terminated while in the right side is -OH terminated. The charge scale starts from 3.6 (dark) to 4.0 (white).

latter makes it smaller when a -OH termination is used instead of hydrogen. In the text of our manuscript we thus carefully discuss these two mechanisms.

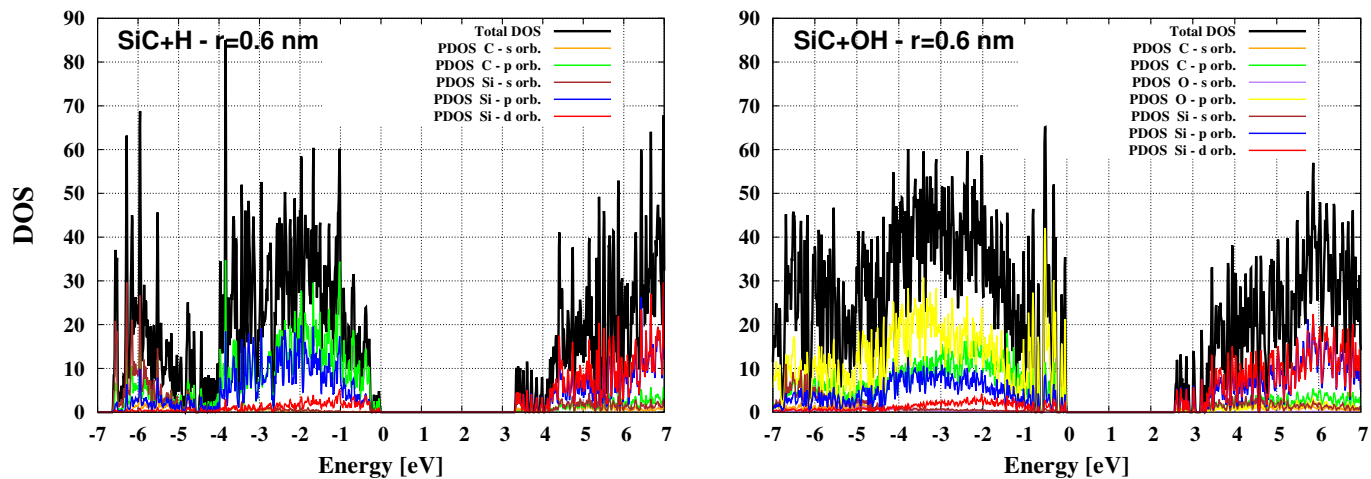


Figure S6: Total and Projected DOS of SiC NWs with diameter equal to 1.2 nm for both -H (left) and -OH (right) terminations

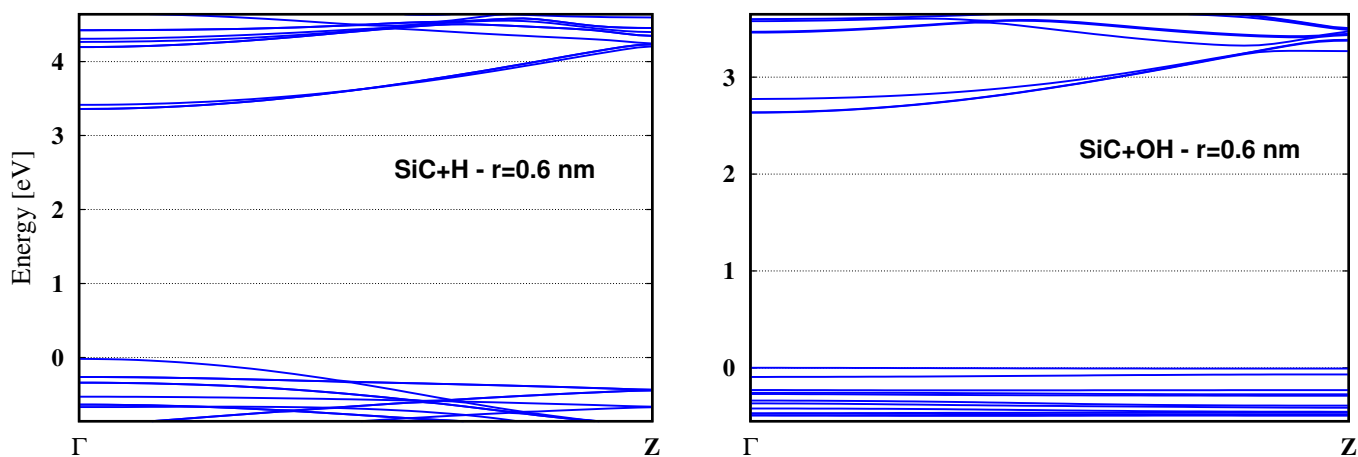


Figure S7: Band structure of SiC NWs with diameter equal to 1.2 nm for -H (left) and -OH (right) terminations.

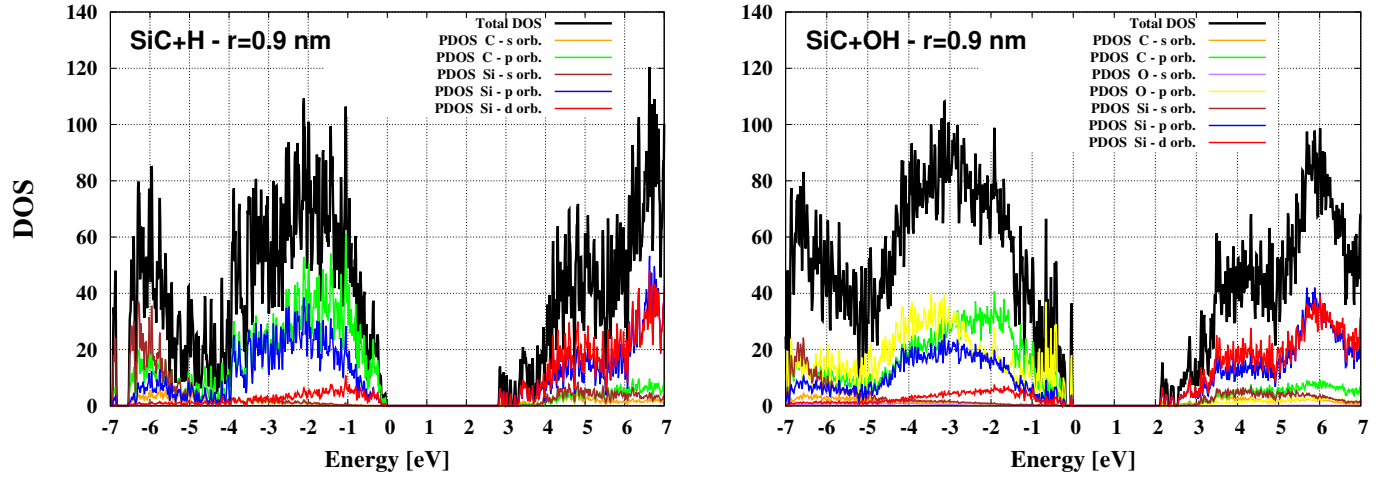


Figure S8: Total and Projected DOS of SiC NWs with diameter equal to 1.8 nm for both $-H$ (left) and $-OH$ (right) terminations.

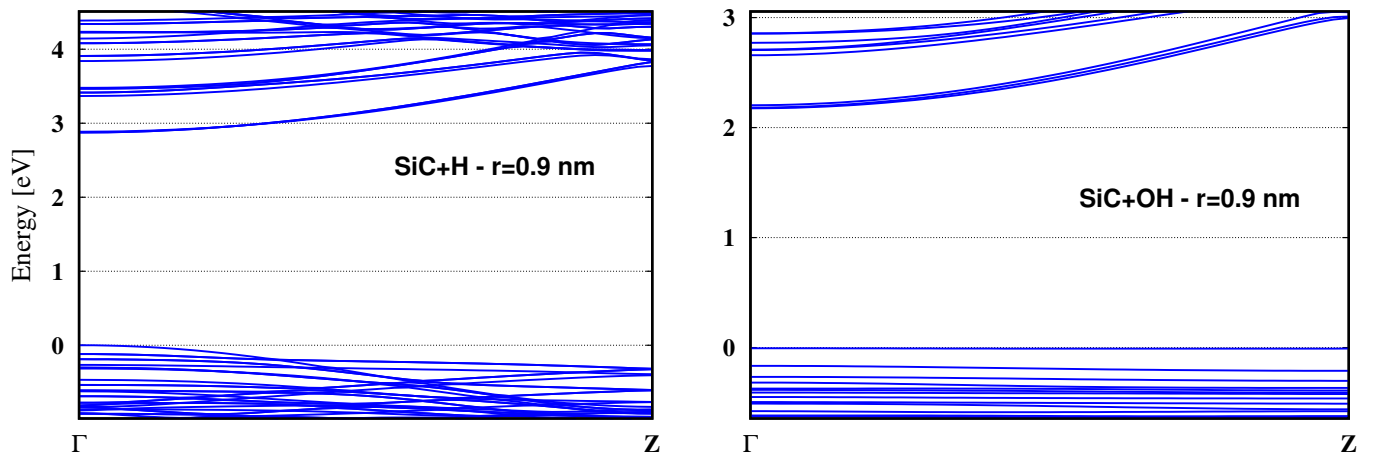


Figure S9: Band structure of SiC NWs with diameter equal to 1.8 nm for $-H$ (left) and $-OH$ (right) terminations.

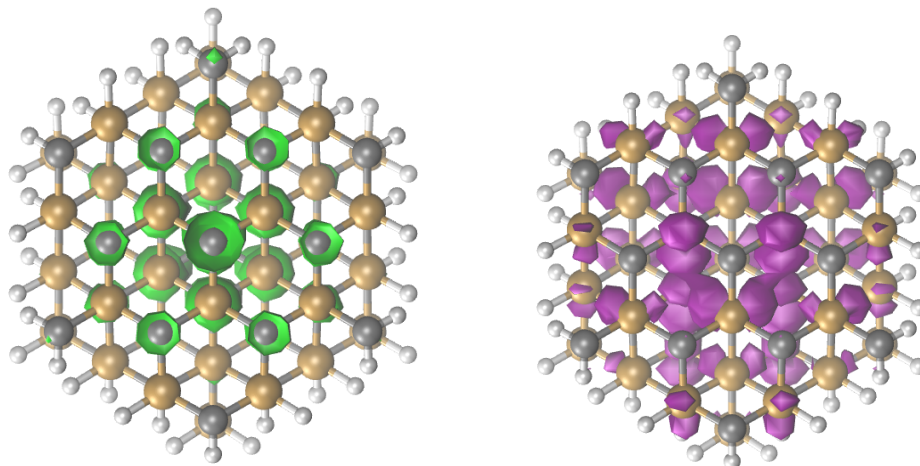


Figure S10: Left) Square modulus of the wave function of the VBM. Right) Square modulus of the CBM wave function. The plots are both referred to the 1.2 nm diameter -H -terminated SiC NW.

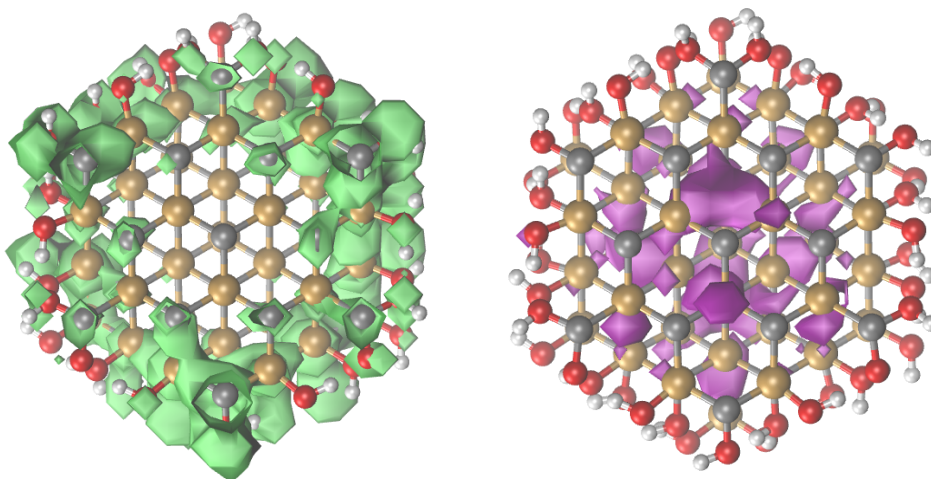


Figure S11: Left) Square modulus of the wave function of the VBM. Right) Square modulus of the CBM wave function. The plots are both referred to the 1.2 nm diameter -OH -terminated SiC NW.

1.2. Adding the silica shell to 3C-SiC NW core and the strategy for SiC/Silica interface modeling

To model the SiO_x outer shell, we coated the 0.6 nm radius SiC core NW. This choice was basically due to the large computational cost of dealing with wires of larger diameter. The LAMMPS program suite, implementing molecular dynamics with reactive potentials (ReaxFF) tailored to reproduce realistic silica and silicon carbide structures [3], was used to build the SiC/ SiO_x NW architecture. Nevertheless, an approach purely based on molecular mechanics is not capable to deliver an accurate representation of the interface between the SiC core and the silica outer shell. In particular, a major problem is related to the description of the decreasing density moving along the radius from the SiC core to the SiO_2 shell. Indeed, the atomic and bond density of the SiC core is much higher than that of silica shell and molecular dynamics cannot be efficiently used to reproduce this effect. To overcome this problem, we decided to use an hybrid approach, in which the bond density is manually decreased by a factor of 2.3 from 42 to 18, using a three-step procedure as exemplified in Fig. S12. This result is reached by saturating the SiC core surface dangling bonds (such as those labeled a, b and c) with oxygen atoms (labeled 1, 2 and 3), by adding a three-coordinated silicon atom (labeled 4) and a further oxygen atom (labeled 5) bound to silicon. This construction was performed saturating 18 free bonds. The others 24 free bonds were saturated two by two, first with oxygen atoms (in a similar way to the previous case), then inserting the Si-O group and finally bridging these three-coordinated silicon atoms two by two with an oxygen atom.

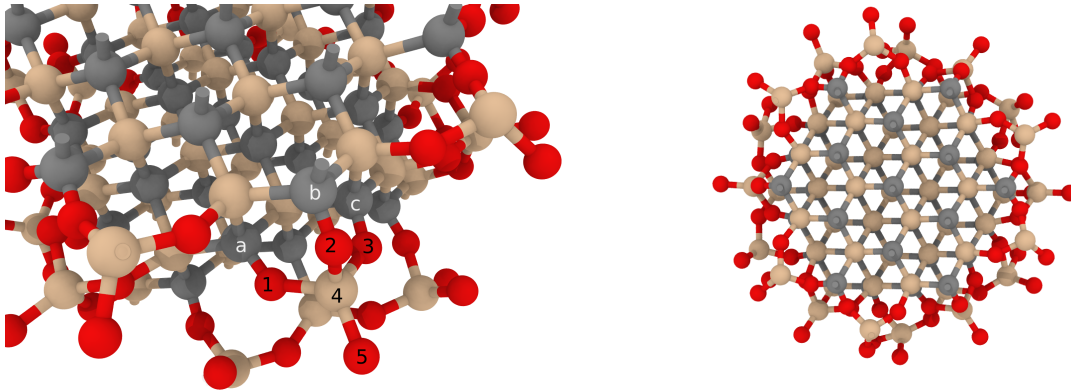


Figure S12: Interfacial bond density reduction procedure. Left panel: our strategy to reduce progressively the number of SiC core surface bonds to that of silica shell can be divided into three steps. First, we saturate all the surface dangling bonds (for example those of atoms indicated by a and c) by oxygen atoms (labeled 1,2,3). Second, a silicon atom (labeled 4) was placed in the proximity of these oxygen atoms in such a way to be three-coordinated. Finally, a further oxygen atom (labeled 5) was bound to silicon. Right panel: a transverse view of the NW core showing the bonds at interface.

As a further step, the silica outer shell was created on the top of the interfacial region by using molecular dynamics. This procedure was accomplished by defining a 3 nm side periodic tetragonal cell surrounding the SiC core and the interface (see Fig. S13). Moreover, silicon and oxygen atoms were added to the simulation cell in 1:2 stoichiometric ratio to reach a density of 2.20 g/cm^3 . SiC and interfacial atomic regions were clamped down while annealing the outer SiO_x shell at 4000 K for 100 ps. Subsequently the temperature was decreased to 10.0 K in 100 ps (using 1 fs timesteps). In the last step of our procedure both the SiC core and the interfacial regions were released and the NW structure was further optimized by DFTB to reach forces among atoms below 0.05 eV/\AA .

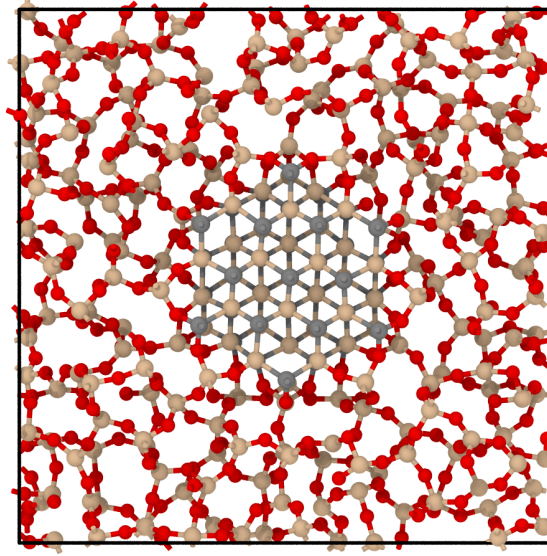


Figure S13: Computational cell used to add the silica outer shell on the top of the SiC core. A number of silicon and oxygen atoms were inserted in the 3 nm side periodic tetragonal box to obtain a mass density of $\sim 2.20 \text{ g/cm}^3$. Finally, the SiC/SiO_x NW has been cut out with a proper choice of shell thickness.

Finally, the SiC/SiO_x NW was obtained by deleting all the atoms that are distant from the wire symmetry axis more than the desired radius. Dangling bonds at the shell surface and some other possibly left within the NW, were passivated by hydrogen atoms.

1.3. Characterization of bond lengths and angles of the SiC/SiO_x core/shell NW model

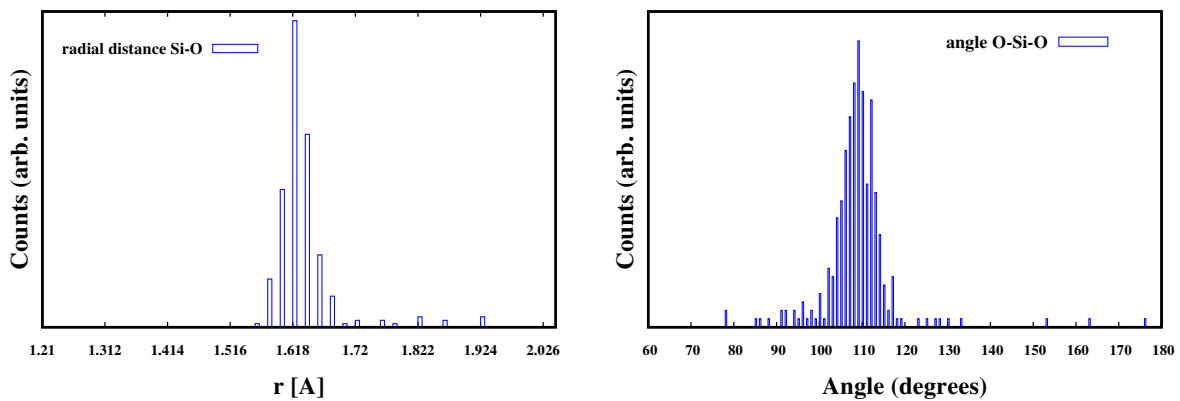


Figure S14: Characterization of SiO_x sample: on the left hand side we plot the distribution of a given radial distance between Si and O atoms; on the right hand side the O-Si-O angles

Geometry characterization of the SiC/SiO_x core/shell NW model was achieved by computing the following quantities:

1. the bond length of Si-O bonds (SiC core keeps its crystalline structure)
2. the bond angles forming O-Si-O atoms

In the left hand side of Fig. S14 we plot the distribution of a given radial distance between Si and O atoms; on the right hand side the O-Si-O angles in the same sample. The peaks compare well with those of silica [4, 5, 6].

1.4. Density of States of SiC/SiO_x core/shell NW

While our SiC/SiO_x NW computational model cannot be realistic due to the large dimensions of a real NW, however provides interesting and reliable information on the electronic band structure of the system, particularly obtained by analyzing the total DOS. Interestingly we notice that the SiC/SiO_x NW show a band gap equal to that of the same dimension SiC core NW saturated by -OH groups. This can be rationalized by noticing that in the SiC/SiO_x NW the very first layer in close contact to the SiC core contains oxygen atoms. In Fig. S15 we report both the total and projected (orbital-resolved) DOS. PDOS will be useful in the interpretation of XANES spectra to identify the transitions.

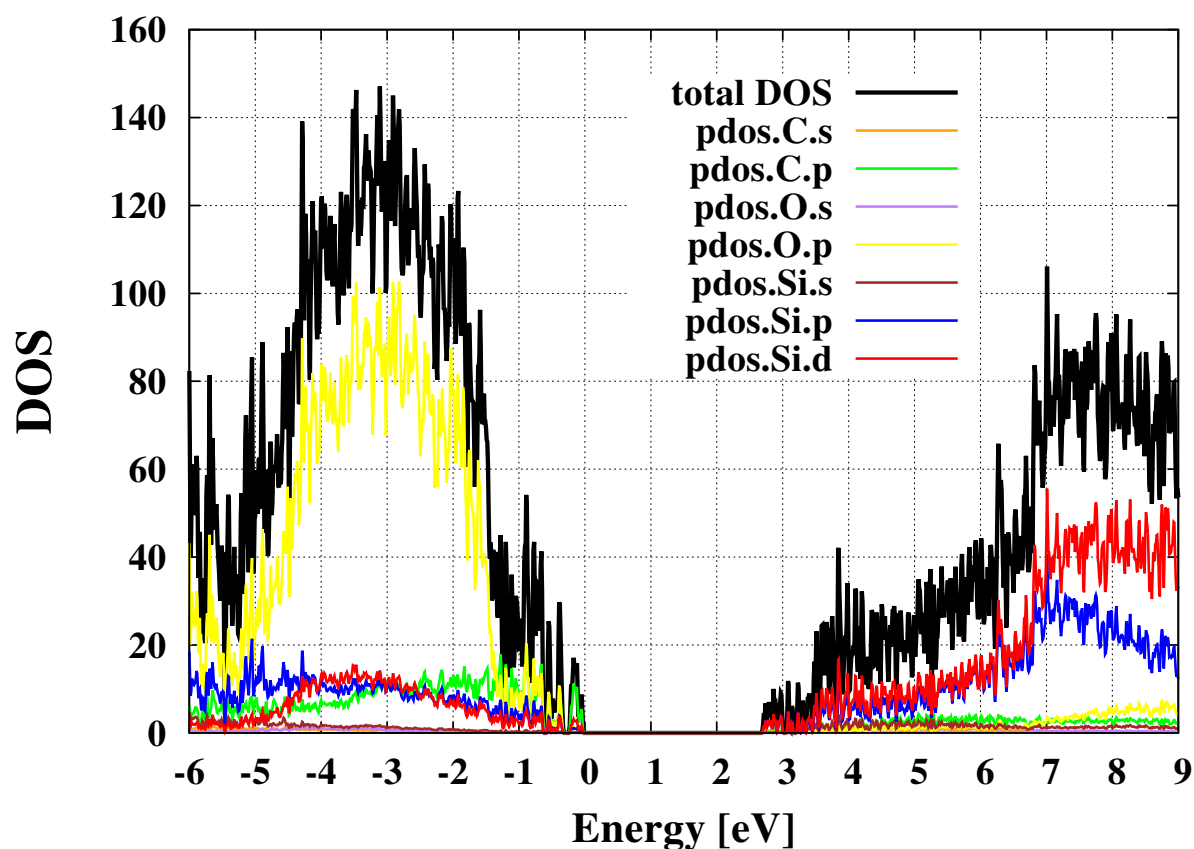


Figure S15: Total and Projected Density of states of our SiC/SiO_x NW model

2. XANES spectra

2.1. SiC bulk XANES spectra simulations

X-ray absorption spectra of the C, O and Si K-edge of the SiC/SiO_x core/shell NW were investigated. To perform these simulations we used the program XSpectra [7, 8], which is part of the Quantum Espresso suite code [9]. XSpectra is able to simulate X-ray absorption dipolar cross sections from the pre-edge to near-edge regions within the single particle approximation. We started our analysis by testing the C K-edge

absorption spectra in crystalline 3C-SiC [10]. The geometric structure of bulk SiC used for these calculations is reported in Fig. S16

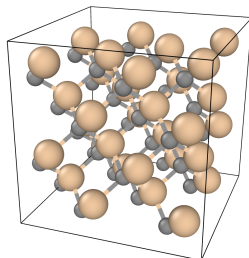


Figure S16: Geometric structure of the 3C-SiC bulk cell, having a cell lattice constant of 8.696 Å and containing 64 atoms

The pseudopotentials (PP) used in these calculations are listed in Tab. S1. The DFT cut-off energy for the wavefunctions was chosen 952.35 eV, while 3809.40 eV for the density.

Atom	PP	1s-PP
C	<i>C.pbe-mt-gipaw.UPF</i>	<i>C.star1s-pbe-mt-gipaw.UPF</i>
Si	<i>Si.pbe-van-gipaw.UPF</i>	<i>Si.star1s-pbe-van-gipaw.UPF</i>
O	<i>O.pbe-van-gipaw.UPF</i>	<i>O.star1s-pbe-van-gipaw.UPF</i>
H	<i>H.pbe-rrkjus.UPF</i>	

Table S1: List of pseudopotentials used for the calculations of the XANES spectra.

In the left hand side of Fig. S17 we report a comparison between our simulations and the experimental data by Liu et al. [10], while in the right hand side we compare our theoretical C K-edge spectrum with that one obtained by Liu [10], finding an overall good agreement. In the right hand side of Fig. S18 we report the XANES spectrum of graphene.

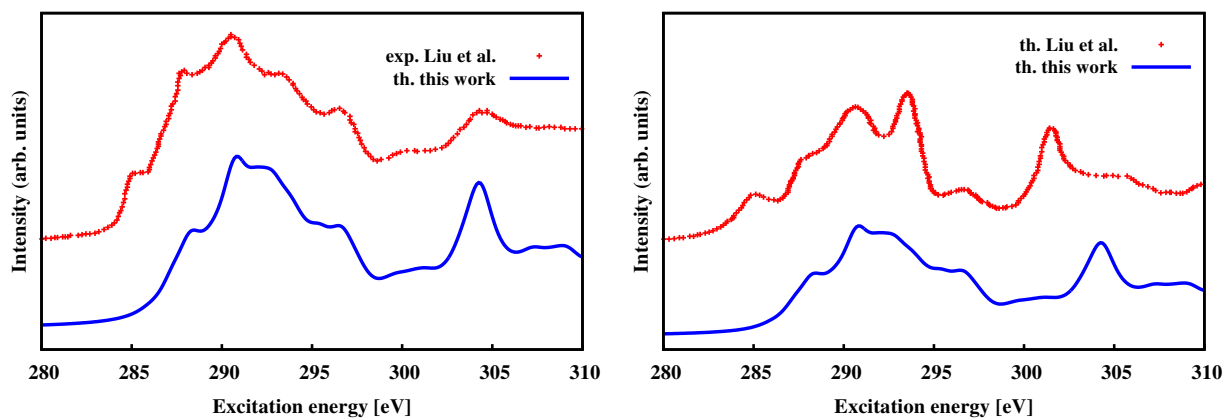


Figure S17: Left: comparison between experimental (from Ref. [10], red curve) and our theoretical C K-edge adsorption spectra of bulk SiC crystal (blue curve). Right: comparison between the theoretical (red curve) C K-edge adsorption spectra of bulk SiC crystal (from Ref. [10]) and our simulations (blue curve).

The good agreement between our simulations and experimental measurements for 3C-SiC makes us confident that the same parameters can be safely used to calculate the C K-edge adsorption spectra of a SiC NWs.

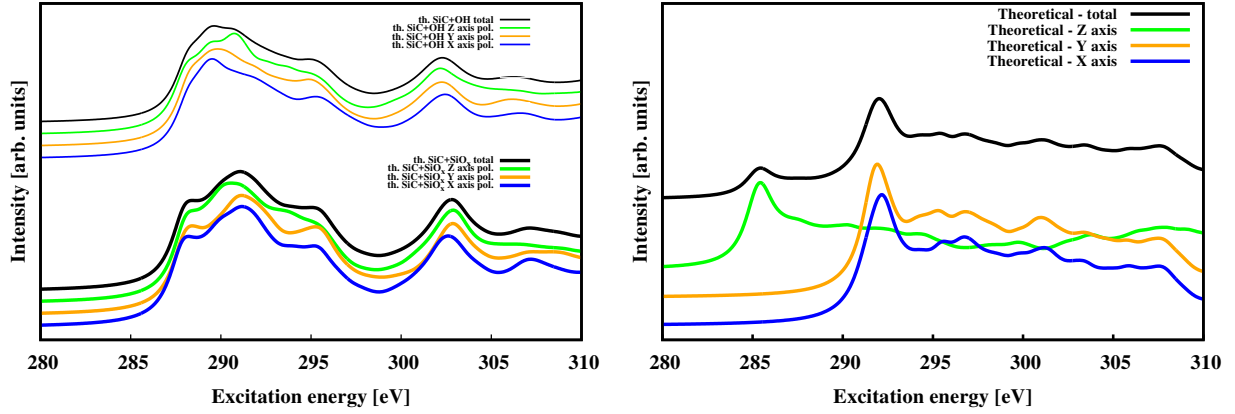


Figure S18: Left: Comparison between calculated C K-edge adsorption spectra of SiC+SiO_x and of SiC+OH nanowires. Right: C K-edge absorption spectra of graphene. Differently colored spectra represent the contribution to the total absorption spectrum of the three polarization directions

2.2. Nanowires XANES spectra calculations

Also in the case of SiC/SiO_x core/shell NWs the presence of the above mentioned peak can be related to *sp*² carbonaceous contaminations present in the SiO_x shell, such as a carboxyl defect within the shell. In Fig. [S19](#) we plot the K edge absorption spectra of our SiC/SiO_x core/shell NW model including this defect.

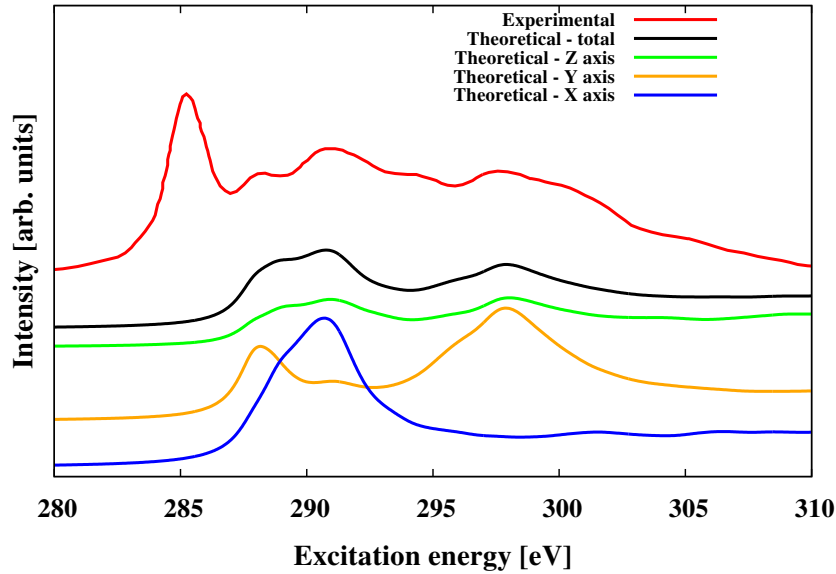


Figure S19: Experimental C K-edge XANES spectrum of as-grown SiC/SiO_x core/shell NWs (red), in comparison with theoretical XANES spectra from our SiC/SiO_x core/shell NW model including a carboxyl defect within the shell.

We notice that by inserting carbonaceous defects in the shell the absorption spectrum presents a different behaviour due to a changed chemical environment of the carbon atoms present in the structure.

2.3. Supporting experimental XANES spectra

Si K-edge XANES spectra of the HF-etched SiC NWs were recorded 1) immediately after the etching process (see red line in Fig. [S20a](#)), and 2) after longer exposure to air (about 60 days, see black line in Fig.

S20a). It can be clearly seen that the feature denoted by B* at 1847 eV can be only detected when the HF-etched NWs were immediately analysed after the etching process. In Fig. **S20b**, the Si K-edge XANES spectrum of SiO_x NWs (without SiC core) is compared to that of as-grown SiC/SiO_x core/shell NWs. It is obvious that the pre-edge peak labeled as A' at 1842 eV is only present in the SiC/SiO_x core/shell NWs. Therefore, it can be reasonably assumed that it originates from the SiC core. We notice that the total electron yield (TEY) mode used to record the experimental XANES spectra is relatively surface-sensitive (i.e., probing depth of a few nm). However, since the SiO_x shell (average thickness of 20 nm **I1**) of our as-grown SiC/SiO_x core/shell NWs can be locally thinner than 20 nm, we are able to detect a small contribution of the internal SiC core.

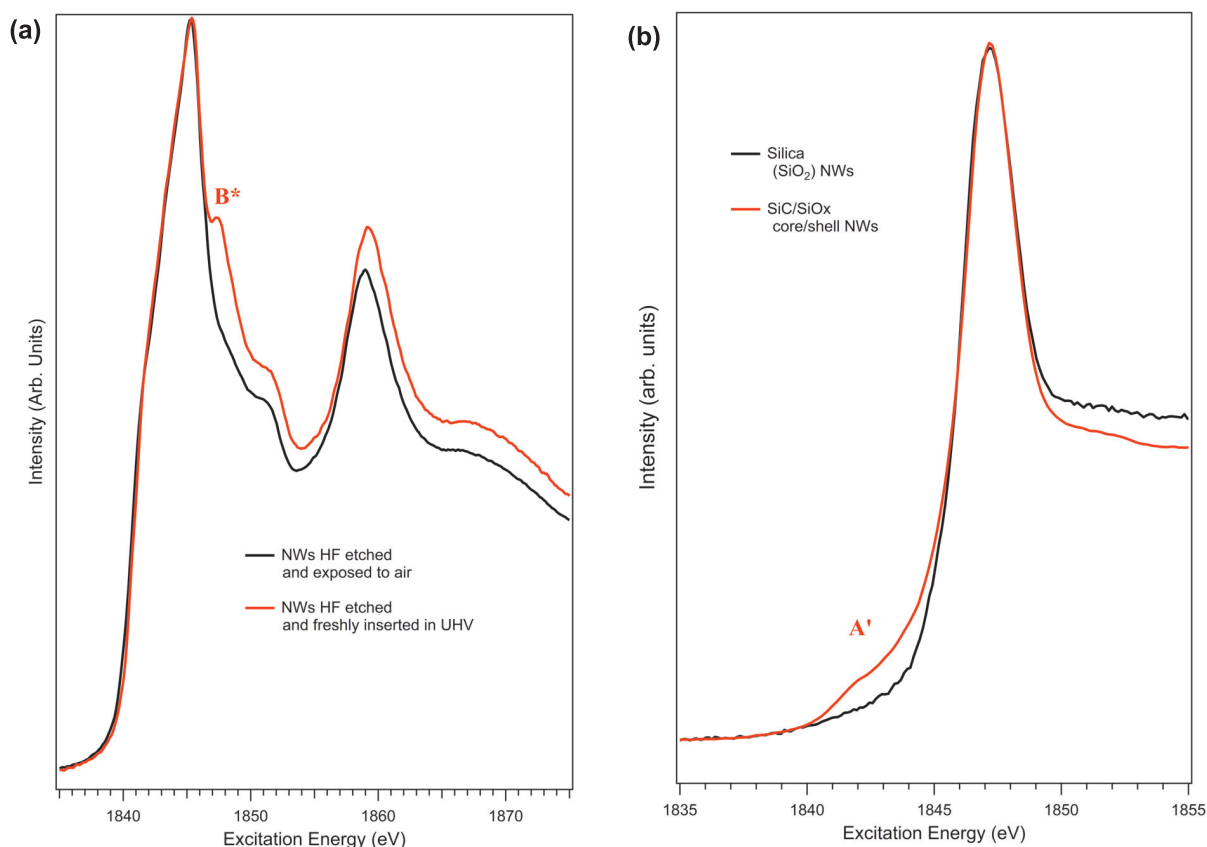


Figure S20: Experimental Si K-edge XANES spectra: (a) HF-etched SiC NWs, which were analysed immediately after the etching process (red), in comparison with a spectrum recorded after longer exposure to air (black); (b) as-grown SiC/SiO_x core/shell NWs (red), in comparison with bare SiO_x NWs grown without SiC core (black).

Additional O K-edge XANES spectra of SiO_x NWs and of (functionalized) SiC/SiO_x core/shell NWs were recorded (see Fig. **S21**) to support the results from simulations that the pre-edge peak at 530 eV mainly stems from unsaturated oxygen. For instance, we can exclude any effects caused by radiation damage, since the SiC/SiO_x core/shell NWs exhibit the pre-edge peak even at acquisition with very low flux ($< 1 \times 10^9$ photons/s) of the incident X-ray beam (see blue line in Fig. **S21**). Furthermore, after surface functionalization of the NWs with a porphyrin molecule via carboxylic acid functional groups (see red line in Fig. **S21**), the pre-edge peak clearly increases. These findings support the idea that the pre-edge peak originates from carbon-containing (functional) groups such as carbonyl and/or carboxyl groups.

[1] B. Aradi, B. Hourahine, T. Frauenheim, Dftb+, a sparse matrix-based implementation of the dftb method, Journal of Physical Chemistry 111.


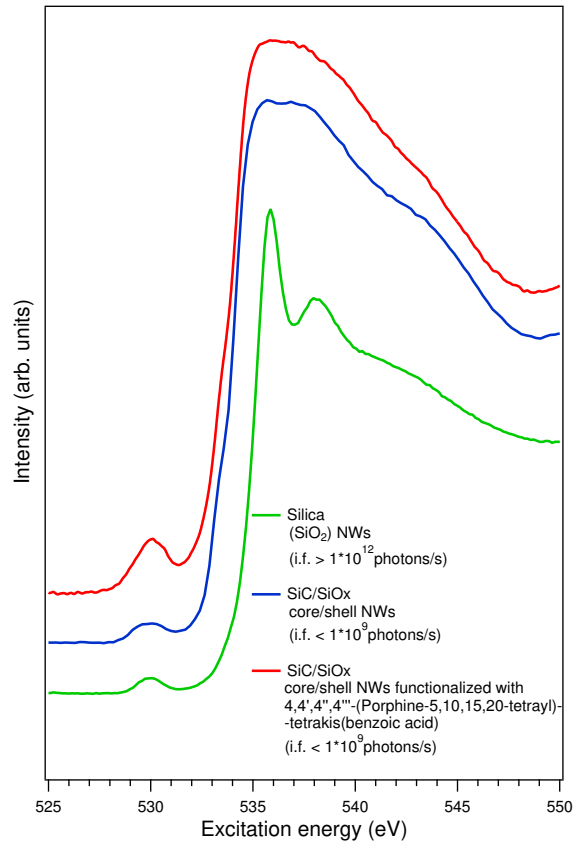


Figure S21: Experimental O K-edge XANES spectra of bare SiO_x NWs grown without SiC core (red) collected with high incident photon flux (i.f.), as-grown SiC/ SiO_x core/shell NWs (blue) collected with low i.f., and SiC/ SiO_x core/shell NWs functionalized with a porphyrin molecule bearing carboxylic acid functional groups (red) collected with low i.f.

- [2] H. Dong, T. Hou, X. Sun, Y. Li, S. Lee, The structures and properties of si/sio₂ core/shell quantum dots studied by density-functional tight-binding calculations, *Applied physics letters* 103.
- [3] A. D. Kulkarni, D. G. Truhlar, S. Goverapet Srinivasan, A. C. T. van Duin, P. Norman, T. E. Schwartzenruber, [Oxygen interactions with silica surfaces: Coupled cluster and density functional investigation and the development of a new reaxff potential](#), *The Journal of Physical Chemistry C* 117 (1) (2013) 258–269. [doi:10.1021/jp3086649](#).
URL <http://dx.doi.org/10.1021/jp3086649>
- [4] J. P. Rino, I. Ebbsjö, R. K. Kalia, A. Nakano, P. Vashishta, [Structure of rings in vitreous sio₂](#), *Physical Review B* 47 (6) (1993) 3053–3062. [doi:10.1103/physrevb.47.3053](#).
URL <http://dx.doi.org/10.1103/PhysRevB.47.3053>
- [5] J. Sarnthein, A. Pasquarello, R. Car, [Model of vitreous sio₂ generated by an ab initio molecular-dynamics quench from the melt](#), *Physical Review B* 52 (17) (1995) 12690–12695. [doi:10.1103/physrevb.52.12690](#).
URL <http://dx.doi.org/10.1103/PhysRevB.52.12690>
- [6] R. M. Van Ginhoven, H. Jónsson, L. R. Corrales, [Silica glass structure generation for ab initio calculations using small samples of amorphous silica](#), *Physical Review B* 71 (2). [doi:10.1103/physrevb.71.024208](#).
URL <http://dx.doi.org/10.1103/PhysRevB.71.024208>
- [7] C. Gougoussis, M. Calandra, A. P. Seitsonen, F. Mauri, [First-principles calculations of x-ray absorption in a scheme based on ultrasoft pseudopotentials: From \$\alpha\$ -quartz to high- \$t_c\$ compounds](#), *Physical Review B* 80 (2009) 075102. [doi:10.1103/PhysRevB.80.075102](#).
URL <https://doi.org/10.1103/PhysRevB.80.075102>
- [8] M. Taillefumier, D. Cabaret, A.-M. Flank, F. Mauri, [X-ray absorption near-edge structure calculations with the pseudopotentials: Application to the k edge in diamond and \$\alpha\$ -quartz](#), *Physical Review B* 66 (2002) 195107. [doi:10.1103/PhysRevB.66.195107](#).
URL <https://link.aps.org/doi/10.1103/PhysRevB.66.195107>
- [9] P. e. a. Giannozzi, [Quantum espresso: a modular and open-source software project for quantum simulations of materials](#), *J. Phys. Condens. Matter* 21 (39) (2009) 395502. [doi:10.1088/0953-8984/21/39/395502](#).

- URL <http://stacks.iop.org/0953-8984/21/i=39/a=395502>
- [10] L. Liu, Y. M. Yiu, T. K. Sham, L. Zhang, Y. Zhang, Electronic structures and optical properties of 6h- and 3c-sic microstructures and nanostructures from x-ray absorption fine structures, x-ray excited optical luminescence, and theoretical studies, *The Journal of Physical Chemistry C* 114 (15) (2010) 6966–6975. [arXiv:http://dx.doi.org/10.1021/jp100277s](http://arxiv.org/abs/http://dx.doi.org/10.1021/jp100277s), [doi:10.1021/jp100277s](https://doi.org/10.1021/jp100277s),
URL <http://dx.doi.org/10.1021/jp100277s>
- [11] F. Fabbri, F. Rossi, G. Attolini, G. Salviati, S. Iannotta, L. Aversa, R. Verucchi, M. Nardi, N. Fukata, B. Dierre, T. Sekiguchi, Enhancement of the core near-band-edge emission induced by an amorphous shell in coaxial one-dimensional nanostructure: the case of sic/sio₂ core/shell self-organized nanowires, *Nanotechnology* 21.

SiC/SiO₂ core/shell nanowires

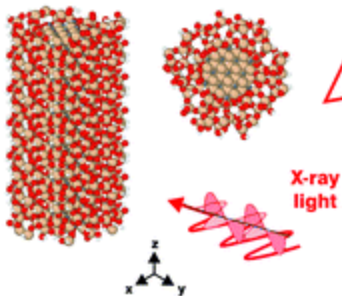

XANES C K-edge

