

Fractal Modelling of Hierarchical Resistant Materials

Alberto Carpinteri, Pietro Cornetti,
Nicola Pugno, Alberto Sapora

Department of Structural Engineering and Geotechnics,
Politecnico di Torino, Torino, Italy

1 Introduction

Many biological materials exhibit a hierarchical structure over more than one length scale. Multiple examples can be given such as bones [1], teeth [2] and shells [3]: bones, for instance, have seven levels of hierarchy, while sea shells present two or three orders of lamellar structures. These materials, at the most elementary level of structural hierarchy, are composed by hard and strong mineral structures embedded in a soft and tough matrix. In bone the mineral platelets are ~ 3 nm thick, in shells their thickness is of ~ 300 nm, while in tooth crystals are ~ 15 - 20 nm thick, with a very high slenderness [4]. Understanding how these structures are related to their mechanical properties emerges, hence, as a primary concern, since it may provide guidance on the development of novel materials with unique properties [5]. Hierarchical structures of biomaterials have been recognized to exhibit self-similarity and to be fractal-like [6]. Size effects on apparent mechanical properties due to the fractal nature of material microstructure have been extensively studied [7-9]. If infinite levels of hierarchy are considered, new universal properties (i.e. scale-invariant quantities) having non-conventional or anomalous physical dimensions must be defined [7-8]. On the other hand, if the hierarchical character is exhibited only over a finite range of scales, as for biological materials, new physical considerations can be drawn. In the present study, the strength and stiffness of hierarchical biomaterials are investigated by means of a fractal approach. The rules of mixture which let estimate the nominal strength of hierarchical materials are firstly presented (Section 2). By exploiting the self-similarity character of the structure, these rules can be condensed in a unique and synthetic manner by means of a fractal approach [10-11] (Section 3). Finally, a new fractal model based on a multiplicative process [12], which takes into account both geometry and material features, is proposed (Section 4).

2 Prediction of strength in hierarchical materials

Let us consider a tensile test on a N -hierarchical fibre-reinforced bar. Its cross-section is composed by hard inclusions embedded in a soft matrix and it is represented in Fig. 1. The nominal stress σ_0 could be evaluated by means of a recursive scheme of rules of mixture as [11]:

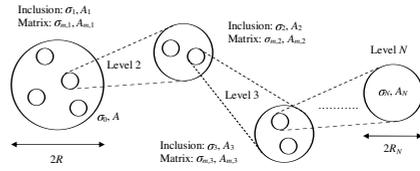


Figure 1: The cross-section of a hierarchical bar.

$$\begin{aligned}
 \sigma_0 &= v_1 \sigma_1 + (1 - v_1) \sigma_{m,1} \\
 \sigma_1 &= v_2 \sigma_2 + (1 - v_2) \sigma_{m,2} \\
 &\dots\dots \\
 \sigma_i &= v_{i+1} \sigma_{i+1} + (1 - v_{i+1}) \sigma_{m,i+1} \\
 &\dots\dots \\
 \sigma_{N-1} &= v_N \sigma_N + (1 - v_N) \sigma_{m,N} \quad ,
 \end{aligned}
 \tag{1}$$

where σ_i and $\sigma_{m,i}$ denote the stresses in the hard and soft phases, respectively, and v_i is the volumetric fraction of inclusions at the i -level (the nanostructure of bones, for instance, shows a mineral to matrix volume ratio in the order of 1 to 2.). The values of the material properties at each level hence depend on those of the preceding levels.

In the case of round (or square)-shaped inclusions at each level, v_i could be expressed in the following form:

$$v_i = n_{h_i} \left(\frac{R_i}{R_{i-1}} \right)^2 \tag{2}$$

being n_{h_i} the number of inclusions and $R_i \sim \sqrt{A_i}$ their mean average radius. Henceforth, the area of the cross-section of the bar A_0 and its characteristic dimension R_0 will be denoted simply by A and R , respectively.

Note that the rules of mixture (Eq. 1) involve, at each step, only the hard phase (i.e., the inclusions, Fig. 1). Although experimental data [13] show that the properties of the matrix may vary at each level, it is often assumed, for the sake of simplicity, that they do not change, i.e., $\sigma_{m,i} = \sigma_m$. In such a case Eq. 1 can be rewritten via a bottom-up approach as:

$$\sigma_0 = \left(\prod_{i=1}^N v_i \right) \sigma_N + \left(1 - \prod_{i=1}^N v_i \right) \sigma_m = v_r \sigma_N + (1 - v_r) \sigma_m, \quad (3)$$

where v_r is the total volumetric fraction of inclusions.

3 Fractal model: constant matrix properties

Natural optimization suggests self-similar structures [14], for which $R_i/R_{i-1} = 1/\delta$ and $n_{h_i} = n_h$; thus, $v_i = v$ and $v_r = v^N$. Thanks to self-similarity, further considerations based on fractal geometry naturally rise up. Particularly, if the hierarchical levels were infinite ($N \rightarrow \infty$), the domain of inclusions would result into a fractal set of dimension D :

$$D = \frac{2 \ln n_h}{\ln n_h - \ln v} = \frac{\ln n_h}{\ln \delta}, \quad (4)$$




Figure 2: The Sierpinski carpet ($D = 1.89$) at different levels of observation.

where $0 < D < 2$. See, for instance, the Sierpinski carpet displayed in Fig. 2.

Since a finite range of scales is taken into account, the total volumetric content of inclusions v_r can be modelled as [11]:

$$v_r = v^N = \left(\frac{R_N}{R} \right)^{2-D}. \quad (5)$$

Thus, by substituting Eq. 5 into Eq. 3:

$$\sigma_0 = \left(\frac{R_N}{R} \right)^{2-D} \sigma_N + \left(1 - \left(\frac{R_N}{R} \right)^{2-D} \right) \sigma_m \approx \left(\frac{R_N}{R} \right)^{2-D} \sigma_N, \quad (6)$$

which predicts that the nominal strength σ_0 decreases as the size increases ($R \rightarrow \infty$) i.e. “smaller is stronger”. The approximation in Eq. 6 keeps true as long as $\sigma_N \gg \sigma_m$, a condition which is usually satisfied.

Note that, according to Eq. 6, the stress levels always remain two, whatever is the hierarchical level of the material. The same scaling law is valid for stiffness.

4 Fractal model: variable matrix properties

In the previous section a scaling law for strength in hierarchical materials has been derived, involving the fractal dimension related to the distribution of inclusions (Eq. 4). This model is based on the simplifying hypothesis of identical matrix properties at each scale level (Eq. 3). On the other hand, as pointed out in Section 2, different properties of the matrix are often noticed at different levels. In order to consider also this feature, a new model is proposed, based on a multiplicative process [12], which will be shown to provide a simple and natural extension of Eq. 6.

Let us suppose that the ligament, which is apparently homogeneous at the macro-scale, is divided into n equal parts: the stiffness is allocated such that n_h cells are enriched by a factor Φ , and n_m cells are depleted by a factor φ . Naturally, $n_h + n_m = n = R^2/R_l^2$. If the condition of perfect bonding between inclusions and matrix is satisfied, the same repartition occurs for stresses:

$$A\sigma_0 = A_1\sigma_1 + A_{m,1}\sigma_{m,1} = \left(\frac{n_h}{n}\Phi + \frac{n_m}{n}\varphi \right) A\sigma_0, \quad (7)$$

where A_i now denotes the total area of inclusions at the level i .

The relationship between Φ and φ can be obtained by imposing the condition that the critical applied force must be the same; from Eq. 7, in formulae:

$$\frac{n_h}{n}\Phi + \frac{n_m}{n}\varphi = 1, \quad (8a)$$

and thus

$$\varphi = \frac{n - n_h\Phi}{n_m}. \quad (8b)$$

Since negative values of parameters Φ and φ lack a physical meaning, it can be deduced from Eq. 8b that $\Phi \in (1, n/n_h)$ and $\varphi \in (0, 1)$.

At the following level, the problem is renormalized so that the “enriched” cells are structured exactly in the same way:

$$A_1\sigma_1 = A_2\sigma_2 + A_{m,2}\sigma_{m,2} = \left(\left(\frac{n_h}{n} \right)^2 \Phi^2 + \frac{n_h n_m}{n^2} \Phi \varphi \right) A\sigma_0. \quad (9)$$

Note that this approach is consistent with Eq. 1. At the generic level N , iterating such a procedure yields:

$$F = A\sigma_0 = A_N\sigma_N + \sum_{j=1}^N A_{m,j}\sigma_{m,j}, \quad (10)$$

where

$$A_N = \left(\frac{n_h}{n}\right)^N A, \quad (11a)$$

$$\sigma_N = \Phi^N \sigma_0. \quad (11b)$$

The material properties are hence distributed in a non-homogeneous way to form a hierarchical structure with different characteristics at different length scales. The distribution process here proposed (Eq. 10) is equivalent to assuming that the ratio between the Young's moduli of matrix and inclusions remains constant at each level. By expressing Eqs. 10a,b as a function of N and equalling the two expressions, the relationship between the nominal strength σ_0 and the strength of inclusions at level N can be obtained:

$$\sigma_0 = \left(\frac{A_N}{A}\right)^{\frac{\log \Phi}{\log(n/n_h)}} \sigma_N. \quad (12)$$

Finally, since:

$$\frac{A_n}{A} = \left(\frac{R_N}{R}\right)^{\frac{2 \log(n/n_h)}{\log n}}, \quad (13)$$

substituting Eq. 13 into Eq. 12, yields:

$$\sigma_0 = \left(\frac{R_N}{R}\right)^{D^*} \sigma_N, \quad (14)$$

where

$$D^* = \frac{2 \log \Phi}{\log n} = D \frac{\log \Phi}{\log n_h}, \quad \Phi \in (1, n/n_h). \quad (15)$$

Eqs. 14-15 describe the nominal strength dependency not only on the volume fraction of inclusions (geometric effect, by D), but also on the nature of such inclusions (material effect, by Φ). Note that, in the homogeneous case ($\Phi = 1$), Eq. 15 provides $D^* = 0$ and consequently $\sigma_0 = \sigma_N$ (Fig. 3). On the other hand, if the specimen is made only of inclusions ($\Phi = n/n_h$), it is not difficult to demonstrate that $D^* = 2 - D$ and the same scaling predicted by Eq. 6 is recovered (Fig. 3).

The present model, by modelling different matrix properties at each level, can hence be considered as an extension of the model presented in Section 3 [11], which is based on purely geometrical considerations.

Under the hypothesis mentioned above, the same scaling occurs clearly for stiffness:

$$E_0 = \left(\frac{R_N}{R} \right)^{D^*} E_N, \quad (16)$$

where E_0 and E_N are the Young's moduli of the bar and of the inclusions at level N , respectively, and D^* is provided by Eq. 15.

5 Conclusions

In this work, the strength and hardness of hierarchical materials are investigated. The study has focused on the behaviour of biomaterials subjected to uniaxial loading. Despite these hierarchical structures show a self-similarity character only over a finite range of scales, it is possible to model their scaling properties at each level by means of a fractal approach. Recursive relationships are presented, based on a renormalization group transformation.

6 Literature

- [1] J.D. Currey: The Mechanical Adaptations of Bones. Princeton University Press, New York 1984.
- [2] H. Warshawsky: Organization of crystals in enamel. Anatomical Record 224 (1989): 242-262.
- [3] J.D. Currey: Mechanical properties of mother of pearl in tension. Proceedings of the Royal Society of London B 196 (1977): 443-463.
- [4] H. Gao: Application of fracture mechanics concepts to hierarchical biomechanics of bone and bone-like materials. Int J Fract 138 (1996): 101-137.

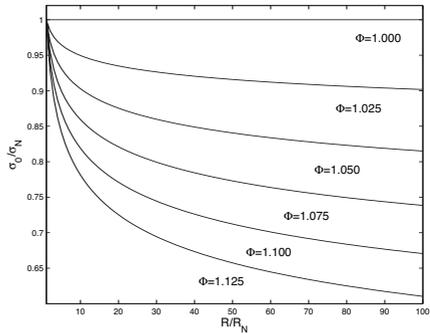


Figure 3: Scaling law of the nominal strength σ_0 for different values of Φ ($n = 9, n_n = 8$).

- [5] P. Fratzl, R. Wienkammer: Nature's hierarchical materials. *Progress in Materials Science* 52 (2007): 1263-1334.
- [6] R. Lakes: Materials with structural hierarchy. *Nature* 361 (1996): 511-15.
- [7] A. Carpinteri: Fractal nature of material microstructure and size effects on apparent mechanical properties. *Mechanics of Materials* 18 (1994): 89-101.
- [8] A. Carpinteri: Scaling laws and renormalization groups for strength and toughness of disordered materials. *International Journal of Solids and Structures* 31 (1994): 291-302.
- [9] A. Carpinteri, N. Pugno: Are scaling laws on strength of solids related to mechanics or geometry? *Nature materials* 4 (2005): 421-23.
- [10] N. Pugno: Mimicking naces with super-nanotubes for producing optimized super-composites. *Nanotechnology* 17 (2006): 5480-84.
- [11] N. Pugno, A. Carpinteri: Design of micro-nanoscale bio-inspired hierarchical materials. *Philosophical Magazine Letters* 88 (2008): 397- 405.
- [12] C. Halsey, M. Jensen, L. Kadanoff, I. Procaccia, B. Shraiman: Fractal measures and their singularities: The characterization of strange sets. *Physical Review A* 33 (1986): 1141-1151.
- [13] H.C. Lee, J. Gurland: Hardness and deformation of cemented tungsten carbide. *Materials science and engineering* 33 (1978): 125-133.
- [14] H.J. Brown, G.B. West: *Scaling in biology*. Oxford University Press, Oxford 1999.
- [15] J. Feder: *Fractals*. Plenum Press, New York 1988.

Contact

Nicola Pugno,

Department of Structural Engineering and Geotechnics, Politecnico di Torino,

Corso Duca degli Abruzzi 24, 10129, Torino, Italy

e-mail: nicola.pugno@polito.it

